

NASA/CR—1999-208676



Analysis of Multiple Cracks in an Infinite Functionally Graded Plate

N.I. Shbeeb, W.K. Binienda, and K.L. Kreider
University of Akron, Akron, Ohio

February 1999

The NASA STI Program Office . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) Program Office plays a key part in helping NASA maintain this important role.

The NASA STI Program Office is operated by Langley Research Center, the Lead Center for NASA's scientific and technical information. The NASA STI Program Office provides access to the NASA STI Database, the largest collection of aeronautical and space science STI in the world. The Program Office is also NASA's institutional mechanism for disseminating the results of its research and development activities. These results are published by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA's counterpart of peer-reviewed formal professional papers but has less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.

- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or cosponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services that complement the STI Program Office's diverse offerings include creating custom thesauri, building customized data bases, organizing and publishing research results . . . even providing videos.

For more information about the NASA STI Program Office, see the following:

- Access the NASA STI Program Home Page at <http://www.sti.nasa.gov>
- E-mail your question via the Internet to help@sti.nasa.gov
- Fax your question to the NASA Access Help Desk at (301) 621-0134
- Telephone the NASA Access Help Desk at (301) 621-0390
- Write to:
NASA Access Help Desk
NASA Center for Aerospace Information
7121 Standard Drive
Hanover, MD 21076

NASA/CR—1999-208676



Analysis of Multiple Cracks in an Infinite Functionally Graded Plate

N.I. Shbeeb, W.K. Binienda, and K.L. Kreider
University of Akron, Akron, Ohio

Prepared under Grant NAG3-2201

National Aeronautics and
Space Administration

Lewis Research Center

February 1999

Acknowledgments

This work was supported in part by NASA Lewis Research Center through grant NAG3-2201 and by the University of Akron. We are grateful to Dr. Gary Halford at NASA for his helpful suggestions and encouragement.

Available from

NASA Center for Aerospace Information
7121 Standard Drive
Hanover, MD 21076
Price Code: A04

National Technical Information Service
5285 Port Royal Road
Springfield, VA 22100
Price Code: A04

Analysis of Multiple Cracks in an Infinite Functionally Graded Plate

N. I. Shbeeb, W. K. Binienda and K. L. Kreider

University of Akron

Akron, Ohio

Abstract

A general methodology was constructed to develop the fundamental solution for a crack embedded in an infinite non-homogeneous material in which the shear modulus varies exponentially with the y coordinate (thickness). The fundamental solution was used to generate a solution to fully interactive multiple crack problems for stress intensity factors and strain energy release rates. Parametric studies were conducted for two crack configurations. The model displayed sensitivity to crack distance, relative angular orientation, and to the coefficient of nonhomogeneity.

Introduction

One of the disadvantages of composites is the mismatch of the thermal expansion coefficients between its constituents. This mismatch produces residual stresses, which may initiate debonding, delamination, and micro-cracks. For example, application of ceramics as a thermal coating for a metal substrate often produce debonding at the interface after a small number of thermo-mechanical load cycles. In order to minimize the mismatch between the ceramics and metal a new technology was developed. This technology allows fully tailored processing of materials and interfacial zones with predetermined continuously varying mechanical properties, that are known as Functionally Graded Materials (FGM) (see Asish et. al., 1997 and Holt et. al., 1993).

FGM could be described, as two-phase particulate composites wherein the volume fraction of its constituents differs continuously in the thickness direction (see Niino and Maeda, 1990; Hirano and Yamada, 1988; Hirano et. al., 1988; and Kawasaki and Watanabe R., 1990). This implies that the composition profile could be tailored to give the appropriate thermomechanical properties. Their physical properties can be determined either experimentally or using higher order theory for FGMs developed by Aboudi, Pindera and Arnold (1997).

Delale and Erdogan (1983) solved the crack problem for a nonhomogeneous plane. The authors considered the plane elasticity problem, in which the material is isotropic, has a constant Poisson's ratio (ν), and the Young's modulus (E) is of an exponential form varying in the x -direction, namely,

$$E(x) = E_0 e^{\beta x} \quad (1)$$

where β is a non-homogeneity constant and E_0 the Young modulus of the homogeneous material. They found that Poisson's ratio did not have much effect on the resulting stress intensity factors. And that the strain-energy release rate at the crack embedded in the portion of the medium with higher stiffness is lower than that corresponding to the crack tip in the less stiff side of the material. Hence, the crack will grow in the direction of the less stiff material.

Also, Delale and Erdogan (1988) solved the collinear crack problem for two dissimilar homogeneous elastic half-planes bonded to a very thin nonhomogeneous layer. The elastic properties of the interfacial material varied continuously between those of the two semi-infinite planes. The Airy stress function was used in their formulation of the solution in which it was assumed that it is composed of two functions, one is associated

with an infinite plane containing the crack on the x-axis, while the second is an uncracked strip. Their results showed that if the crack location approaches the less stiff material, the strain energy release rate increases.

It can be noticed that multiple oriented crack problems embedded in a non-homogeneous infinite plate have not yet been addressed. Thus the scope of this work will deal with the general solution to a single and multiple oriented cracks embedded in a nonhomogeneous infinite plate. It is assumed that the FGM has a constant Poisson's ratio and the shear modulus is of an exponential form. The solution is valid for both plane stress and plane strain.

General Problem Formulation

The solution of the mixed boundary value problems for stress intensity factors or strain energy release rates at a crack tip is obtained from the perturbation part of the problem, see Figure 1. Before any particular problem is addressed, the general strategy of solution is discussed in this section.

Assume that there are two states of stresses, one is associated with a local coordinate system (x_1-y_1) in an infinite plate, while the other is associated with boundaries of a finite plate defined in a structural coordinate system $(x-y)$. The crack lies on the x_1 -axis, which is at an angle θ from the x-axis. In the case of infinite plate problems only the first state of stress exists, but for the general problem the total stresses in the local coordinate system are expressed as:

$$\begin{aligned}\sigma_{y_1y_1}^T(x_1, y_1) &= \sigma_{y_1y_1}^{(1)}(x_1, y_1) + \sigma_{y_1y_1}^{(2)}(x_1, y_1) \\ \tau_{y_1y_1}^T(x_1, y_1) &= \tau_{y_1y_1}^{(1)}(x_1, y_1) + \tau_{y_1y_1}^{(2)}(x_1, y_1)\end{aligned}\tag{2}$$

where,

$$\begin{aligned}
\sigma_{y_1 y_1}^{(2)}(x_1, y_1) &= \sin^2(\theta)\sigma_{xx}(x, y) + \cos^2(\theta)\sigma_{yy}(x, y) - 2\sin(\theta)\cos(\theta)\tau_{xy}(x, y) \\
\tau_{y_1 y_1}^{(2)}(x_1, y_1) &= -\sin(\theta)\cos(\theta)\sigma_{xx}(x, y) + \sin(\theta)\cos(\theta)\sigma_{yy}(x, y) \\
&\quad + (\cos^2(\theta) - \sin^2(\theta))\tau_{xy}(x, y) \\
x &= x_1 \cos(\theta) - y_1 \sin(\theta) \\
y &= x_1 \sin(\theta) + y_1 \cos(\theta)
\end{aligned}$$

The stress boundary conditions obtained from the perturbation problem are:

$$\begin{aligned}
-p_1(x_1) &= \lim_{y_1 \rightarrow 0} \sigma_{y_1 y_1}^T(x_1, y_1) \\
-p_2(x_1) &= \lim_{y_1 \rightarrow 0} \tau_{x_1 y_1}^T(x_1, y_1)
\end{aligned} \tag{3}$$

where $p_1(x_1)$ and $p_2(x_1)$ are the normal and shear tractions of the inner crack surfaces.

Upon substitution of (2) into (3) the boundary conditions becomes:

$$-p_1(x_1) = \lim_{y_1 \rightarrow 0} \sigma_{y_1 y_1}^{(1)}(x_1, y_1) + \lim_{y_1 \rightarrow 0} \sigma_{y_1 y_1}^{(2)}(x_1, y_1) \tag{4}$$

$$-p_2(x_1) = \lim_{y_1 \rightarrow 0} \tau_{x_1 y_1}^{(1)}(x_1, y_1) + \lim_{y_1 \rightarrow 0} \tau_{x_1 y_1}^{(2)}(x_1, y_1) \tag{5}$$

It is noticed that the principal part will be produced from the first part of (4) and (5). The most general form of the stresses are expressed as:

$$\begin{aligned}
\sigma_{y_1 y_1}^{(1)}(x_1, y_1) &= \frac{1}{2\pi} \int_a^b K_{1j}^{(1)}(x_1, y_1, t) f_j(t) dt \\
\tau_{x_1 y_1}^{(1)}(x_1, y_1) &= \frac{1}{2\pi} \int_a^b K_{2j}^{(1)}(x_1, y_1, t) f_j(t) dt \\
\sigma_{y_1 y_1}^{(2)}(x_1, y_1) &= \frac{1}{2\pi} \int_a^b K_{1j}^{(2)}(x_1, y_1, t) f_j(t) dt \\
\tau_{x_1 y_1}^{(2)}(x_1, y_1) &= \frac{1}{2\pi} \int_a^b K_{2j}^{(2)}(x_1, y_1, t) f_j(t) dt \quad \text{for } a < (x_1, t) < b
\end{aligned} \tag{6}$$

where f_j are so called auxiliary functions defined as derivatives with respect to x_1 of displacement jumps along the crack. The kernels are expressed as:

$$\begin{aligned} K_{ij}^{(1)}(x_1, y_1, t) &= \int_{-\infty}^{\infty} X_{ij}^{(1)}(\alpha, y_1) e^{\alpha i(x_1 - t)} d\alpha \\ K_{ij}^{(2)}(x_1, y_1, t) &= \int_{-\infty}^{\infty} X_{ij}^{(2)}(\alpha, x_1 \cos \theta - y_1 \sin \theta) e^{\alpha i(x_1 \sin \theta + y_1 \cos \theta - t)} d\alpha \end{aligned} \quad (7)$$

The expressions of $X_{ij}^{(1)}$ and $X_{ij}^{(2)}$ depend on the stress and displacement continuity of the problem. If $X_{ij}^{(1)}$ do not vanish as $|\alpha|$ approaches infinity then an asymptotic analysis is done to separate the singular part from the regular. Consequently equation (7) can be integrated numerically.

As $|\alpha|$ approaches infinity equation (7) becomes:

$$\begin{aligned} K_{ij}^{(1)}(x_1, y_1, t) &= \int_{-\infty}^{\infty} X_{ij}^{(1)}(\alpha) e^{-|\alpha|y_1 + i\alpha(x_1 - t)} d\alpha \\ K_{ij}^{(2)}(x_1, y_1, t) &= \int_{-\infty}^{\infty} X_{ij}^{(2)}(\alpha) e^{-|\alpha|(x_1 \sin \theta + y_1 \cos \theta) + i\alpha(x_1 \cos \theta - y_1 \sin \theta - t)} d\alpha \end{aligned} \quad (8)$$

Substituting equation (8) into (6), the following is obtained:

$$\begin{aligned} \sigma_{y_1 y_1}^{(1)}(x_1, y_1) &= \frac{1}{2\pi} \int_{-\infty}^{\infty} X_{1j}^{(1)}(\alpha) e^{-|\alpha|y_1 + i\alpha(x_1 - t)} d\alpha \int_a^b f_j(t) dt \\ \tau_{x_1 y_1}^{(1)}(x_1, y_1) &= \frac{1}{2\pi} \int_{-\infty}^{\infty} X_{2j}^{(1)}(\alpha) e^{-|\alpha|y_1 + i\alpha(x_1 - t)} d\alpha \int_a^b f_j(t) dt \end{aligned} \quad (9)$$

$$\begin{aligned} \sigma_{y_1 y_1}^{(2)}(x_1, y_1) &= \frac{1}{2\pi} \int_{-\infty}^{\infty} X_{1j}^{(2)}(\alpha) e^{-|\alpha|(x_1 \sin \theta + y_1 \cos \theta) + i\alpha(x_1 \cos \theta - y_1 \sin \theta - t)} d\alpha \int_a^b f_j(t) dt \\ \tau_{x_1 y_1}^{(2)}(x_1, y_1) &= \frac{1}{2\pi} \int_{-\infty}^{\infty} X_{2j}^{(2)}(\alpha) e^{-|\alpha|(x_1 \sin \theta + y_1 \cos \theta) + i\alpha(x_1 \cos \theta - y_1 \sin \theta - t)} d\alpha \int_a^b f_j(t) dt \end{aligned} \quad (10)$$

Further simplifications can be achieved by taking the limit of equation (9) so that the first terms in equations (4) and (5) can be determined:

$$\lim_{y_1 \rightarrow 0} \left[\frac{1}{2\pi} \int_{-\infty}^{\infty} X_{ij}^{(1)}(\alpha) e^{-|\alpha|y_1 + i\alpha(x_1 - t)} d\alpha \int_a^b f_j(t) dt \right] \quad (11)$$

Assume that $X_{ij}^{(1)}$ have the following asymptotes:

$$\begin{aligned} asy1 &= c_{ij}^{(1)} + id_{ij}^{(1)} \dots \dots \alpha \rightarrow +\infty \\ asy2 &= c_{ij}^{(1)} - id_{ij}^{(1)} \dots \dots \alpha \rightarrow -\infty \end{aligned} \quad (12)$$

Splitting equation (12) at $\alpha=0$ into two parts and making the change of variable for the part from $-\infty$ to 0 by letting $\alpha=-\beta$, adding and subtracting (12) from (11) and taking the limit as $y_1 \rightarrow 0$, the following is obtained:

$$\begin{aligned} &\frac{1}{2\pi} \int_0^{\infty} \{ [X_{ij}^{(1)}(\alpha) + X_{ijc}^{(1)}(\alpha) - 2c_{ij}^{(1)}] \cos(\alpha(t - x_1)) + \\ &[X_{ijc}^{(1)}(\alpha) - X_{ij}^{(1)}(\alpha) + 2id_{ij}^{(1)}] i \sin(\alpha(t - x_1)) \} d\alpha + \lim_{y_1 \rightarrow 0} \left[\frac{1}{2\pi} SIP^{(1)} \right] \end{aligned} \quad (13)$$

where, $X_{ijc}^{(1)}(\alpha)$ is the complex conjugate of $X_{ij}^{(1)}(\alpha)$ and the term denoted by $SIP^{(1)}$ is:

$$SIP^{(1)} = \int_0^{\infty} 2e^{-\alpha y_1} \{ c_{ij}^{(1)} \cos(\alpha(t - x_1)) + d_{ij}^{(1)} \sin(\alpha(t - x_1)) \} d\alpha \quad (14)$$

The following integral identities can be used to evaluate equation (14) (Abramowitz and Stegun, 1964):

$$\begin{aligned} \int_0^{\infty} e^{-\alpha n} \cos(m\alpha) d\alpha &= \frac{n}{n^2 + m^2} \\ \int_0^{\infty} e^{-\alpha n} \sin(m\alpha) d\alpha &= \frac{m}{n^2 + m^2} \end{aligned} \quad (15)$$

Hence, it can be shown that (14) becomes,

$$2 \frac{c_{ij}^{(1)} y_1}{(t - x_1)^2 + y_1^2} + 2 \frac{d_{ij}^{(1)} (t - x_1)}{(t - x_1)^2 + y_1^2} \quad (16)$$

where upon taking the limit of (16) and substituting the result into (13) the following expression is obtained:

$$\begin{aligned} & \frac{1}{2\pi} \int_0^{\infty} \{ [X_{ij}^{(1)} + X_{ijc}^{(1)} - 2c_{ij}^{(1)}] \cos(\alpha(t - x_1)) + \\ & [X_{ijc}^{(1)} - X_{ij}^{(1)} + 2id_{ij}^{(1)}] i \sin(\alpha(t - x_1)) \} d\alpha + \frac{1}{\pi} \frac{d_{ij}^{(1)}}{t - x_1} \end{aligned} \quad (17)$$

In some problems the integrand $X_{ij}^{(1)}(\alpha)$ does not converge rapidly to zero, consequently U (where $X_{ij}^{(1)}$ is close to zero) is large, thus for computational efficiency an additional term of the asymptote is taken which is of the order (α^{-1}) , namely:

$$asy11 = \frac{e_{ij}^{(1)}}{\alpha} + i \frac{g_{ij}^{(1)}}{\alpha} \dots \alpha \rightarrow +\infty \quad (18)$$

Equation (17) remains the same if the asymptote (18) is subtracted and added at the same time. It becomes:

$$\begin{aligned} & \frac{1}{2\pi} \int_0^{\infty} \{ [X_{ij}^{(1)}(\alpha) + X_{ijc}^{(1)}(\alpha) - 2(c_{ij}^{(1)} + \frac{e_{ij}^{(1)}}{\alpha})] \cos(\alpha(t - x_1)) + \\ & [X_{ijc}^{(1)}(\alpha) - X_{ij}^{(1)}(\alpha) + 2i(d_{ij}^{(1)} + \frac{g_{ij}^{(1)}}{\alpha})] i \sin(\alpha(t - x_1)) \} d\alpha + \frac{1}{\pi} \frac{d_{ij}^{(1)}}{t - x_1} \\ & + \frac{1}{2\pi} \int_0^{\infty} \frac{2e_{ij}^{(1)} \cos(\alpha(t - x_1))}{\alpha} d\alpha - \frac{1}{2\pi} \int_0^{\infty} \frac{2g_{ij}^{(1)} \sin(\alpha(t - x_1))}{\alpha} d\alpha \end{aligned} \quad (19)$$

To evaluate the last two terms of equation (19) the following identities are used (Abramowitz and Stegun, 1964):

$$\begin{aligned} \int_0^{\infty} \frac{1}{\alpha} \sin(\alpha(t - x_1)) d\alpha &= \frac{\pi}{2} \frac{(t - x_1)}{|t - x_1|} \\ \int_U^{\infty} \frac{1}{\alpha} \cos(\alpha(t - x_1)) d\alpha &= -Ci(U(t - x_1)) \\ &= -(C_0 + \log|U(t - x_1)| + \int_0^{|U(t-x_1)|} \frac{\cos \beta - 1}{\beta} d\beta) \end{aligned} \quad (20)$$

where, C_0 is the Euler constant. The following expression replaces equation (19),

$$\begin{aligned}
& \frac{1}{2\pi} \int_0^\infty \{ [X_{ijc}^{(1)}(\alpha) - X_{ij}^{(1)}(\alpha) + 2i(d_{ij}^{(1)} + \frac{g_{ij}^{(1)}}{\alpha})] i \sin(\alpha(t - x_1)) \} d\alpha \\
& + \frac{1}{2\pi} \int_0^U \{ [X_{ij}^{(1)}(\alpha) + X_{ijc}^{(1)}(\alpha) - 2c_{ij}^{(1)}] \cos(\alpha(t - x_1)) \} d\alpha \\
& + \frac{1}{2\pi} \int_U^\infty \{ [X_{ij}^{(1)}(\alpha) + X_{ijc}^{(1)}(\alpha) - 2(c_{ij}^{(1)} + \frac{e_{ij}^{(1)}}{\alpha})] \cos(\alpha(t - x_1)) \} d\alpha \\
& + \frac{1}{\pi} \frac{d_{ij}^{(1)}}{t - x_1} - \frac{g_{ij}^{(1)}}{2} \frac{(t - x_1)}{|t - x_1|} - \frac{e_{ij}^{(1)}}{\pi} Ci(U(t - x_1))
\end{aligned} \tag{21}$$

The first part of (4) and (5) can be expressed as:

$$\begin{aligned}
\Rightarrow \lim_{y_1 \rightarrow 0} \sigma_{y_1 y_1}^{(1)}(x_1, y_1) &= \frac{1}{\pi} \int_a^b \frac{d_{1j}^{(1)} f_j(t)}{t - x_1} dt + \frac{1}{2\pi} \int_a^b k_{1j}^{(1)}(x_1, t) f_j(t) dt \\
&+ \int_a^b \left[\frac{g_{1j}^{(1)}}{2} \frac{(t - x_1)}{|t - x_1|} - \frac{e_{1j}^{(1)}}{\pi} Ci(U(t - x_1)) \right] f_j(t) dt
\end{aligned} \tag{22}$$

$$\begin{aligned}
\Rightarrow \lim_{y_1 \rightarrow 0} \tau_{x_1 y_1}^{(1)}(x_1, y_1) &= \frac{1}{\pi} \int_a^b \frac{d_{2j}^{(1)} f_j(t)}{t - x_1} dt + \frac{1}{2\pi} \int_a^b k_{2j}^{(1)}(x_1, t) f_j(t) dt \\
&+ \int_a^b \left[\frac{g_{2j}^{(1)}}{2} \frac{(t - x_1)}{|t - x_1|} - \frac{e_{2j}^{(1)}}{\pi} Ci(U(t - x_1)) \right] f_j(t) dt
\end{aligned} \tag{23}$$

where,

$$\begin{aligned}
k_{ij}^{(1)}(x_1, t) &= \int_0^\infty \{ [X_{ijc}^{(1)}(\alpha) - X_{ij}^{(1)}(\alpha) + 2i(d_{ij}^{(1)} + \frac{g_{ij}^{(1)}}{\alpha})] i \sin(\alpha(t - x_1)) \} d\alpha \\
&+ \int_0^U \{ [X_{ij}^{(1)}(\alpha) + X_{ijc}^{(1)}(\alpha) - 2c_{ij}^{(1)}] \cos(\alpha(t - x_1)) \} d\alpha \\
&+ \int_U^\infty \{ [X_{ij}^{(1)}(\alpha) + X_{ijc}^{(1)}(\alpha) - 2(c_{ij}^{(1)} + \frac{e_{ij}^{(1)}}{\alpha})] \cos(\alpha(t - x_1)) \} d\alpha
\end{aligned} \tag{24}$$

A similar procedure is applied procedure to the second terms in equations (4) and (5), expressed in the form shown in (10). The terms denoted by $X_{ij}^{(2)}(\alpha)$ have the following asymptotes:

$$\begin{aligned}
asy3 &= (a_{ij}^{(2)} + ib_{ij}^{(2)})\alpha + c_{ij}^{(2)} + id_{ij}^{(2)} \dots \alpha \rightarrow +\infty \\
asy4 &= (-a_{ij}^{(2)} + ib_{ij}^{(2)})\alpha + c_{ij}^{(2)} - id_{ij}^{(2)} \dots \alpha \rightarrow -\infty
\end{aligned} \tag{25}$$

Simplifications can be made with the use of the integral identities (Abramowitz and Stegun, 1964):

$$\begin{aligned}\int_0^{\infty} \alpha e^{-\alpha n} \cos(m\alpha) d\alpha &= \frac{n^2 - m^2}{(n^2 + m^2)^2} \\ \int_0^{\infty} \alpha e^{-\alpha n} \sin(m\alpha) d\alpha &= \frac{2nm}{(n^2 + m^2)^2}\end{aligned}\quad (26)$$

Hence, the second part of equations (4) and (5) becomes:

$$\begin{aligned}\Rightarrow \lim_{y_1 \rightarrow 0} \sigma_{y_1 y_1}^{(2)}(x_1, y_1) &= \frac{1}{\pi} \int_a^b \left[\frac{a_{1j}^{(2)}(x_1^2 \sin^2 \theta - \cos^2 \theta (t - x_1)^2)}{(x_1^2 \sin^2 \theta + \cos^2 \theta (t - x_1)^2)^2} \right. \\ &\quad + \frac{2b_{1j}^{(2)} x_1 (t - x_1) \sin \theta \cos \theta}{(x_1^2 \sin^2 \theta + \cos^2 \theta (t - x_1)^2)^2} \\ &\quad + \left. \frac{c_{1j}^{(2)} x_1 \sin \theta + 2d_{1j}^{(2)} \cos \theta (t - x_1)}{(x_1^2 \sin^2 \theta + \cos^2 \theta (t - x_1)^2)^2} \right] f_j(t) dt \\ &\quad + \frac{1}{2\pi} \int_a^b k_{1j}^{(2)}(x_1, t) f_j(t) dt\end{aligned}\quad (27)$$

$$\begin{aligned}\Rightarrow \lim_{y_1 \rightarrow 0} \tau_{x_1 y_1}^{(2)}(x_1, y_1) &= \frac{1}{\pi} \int_a^b \left[\frac{a_{2j}^{(2)}(x_1^2 \sin^2 \theta - \cos^2 \theta (t - x_1)^2)}{(x_1^2 \sin^2 \theta + \cos^2 \theta (t - x_1)^2)^2} \right. \\ &\quad + \frac{2b_{2j}^{(2)} x_1 (t - x_1) \sin \theta \cos \theta}{(x_1^2 \sin^2 \theta + \cos^2 \theta (t - x_1)^2)^2} \\ &\quad + \left. \frac{c_{2j}^{(2)} x_1 \sin \theta + 2d_{2j}^{(2)} \cos \theta (t - x_1)}{(x_1^2 \sin^2 \theta + \cos^2 \theta (t - x_1)^2)^2} \right] f_j(t) dt \\ &\quad + \frac{1}{2\pi} \int_a^b k_{2j}^{(2)}(x_1, t) f_j(t) dt\end{aligned}\quad (28)$$

where,

$$\begin{aligned}k_{ij}^{(2)}(x_1, t) &= \int_0^{\infty} \{ [X_{ijc}^{(2)}(\alpha) - X_{ij}^{(2)}(\alpha) + 2i(\alpha b_{ij}^{(2)} + d_{ij}^{(2)}) e^{-\alpha x_1 \sin \theta}] i \sin(\alpha(t - x_1)) \} d\alpha \\ &\quad + \int_0^{\infty} \{ [X_{ij}^{(2)}(\alpha) + X_{ijc}^{(2)}(\alpha) - 2(\alpha a_{ij}^{(2)} + c_{ij}^{(2)}) e^{-\alpha x_1 \sin \theta}] \cos(\alpha(t - x_1)) \} d\alpha\end{aligned}\quad (29)$$

It should be noted that (27) and (28) do not contain any singularity and the asymptotic expansion is applied only for computational efficiency.

Fundamental Solution

The formulated equations in the previous section will be used to solve the problem of radial multiple cracks in an infinite isotropic FGM as depicted in Figure 2. Since dealing with an infinite plate only equations (22), (23) and (24) will be used. But before doing so, the fundamental solution of a single crack is required. Konda and Erdogan (1994) solved the single crack problem using Navier equations. In this work the same problem will be solved using Airy stress function and the shear modulus μ will vary exponentially with the global y-axis.

The shear modulus is defined as follows:

$$\begin{aligned}\mu_2(y) &= \mu_0 e^{\gamma y} \\ \mu_2(x_1, y_1) &= \mu_0 e^{\beta x_1 + \delta y_1} \\ \delta &= \gamma \cos(\theta) \\ \beta &= \gamma \sin(\theta)\end{aligned}\quad (30)$$

where γ , δ , and β are real constants and represent the coefficients of nonhomogeneity.

The Airy stress function $U(x_1, y_1)$ are defined as,

$$\begin{aligned}\sigma_{x_1 x_1}(x_1, y_1) &= \frac{\partial^2 U}{\partial y_1^2} \\ \sigma_{y_1 y_1}(x_1, y_1) &= \frac{\partial^2 U}{\partial x_1^2} \\ \tau_{x_1 y_1}(x_1, y_1) &= -\frac{\partial^2 U}{\partial x_1 \partial y_1}\end{aligned}\quad (31)$$

The stresses and strains are related through:

$$\begin{aligned}\varepsilon_{x_1 x_1}(x_1, y_1) &= \frac{\partial u_1}{\partial x_1} = \frac{1}{8\mu(x_1, y_1)} \left[(\kappa + 1)\sigma_{x_1 x_1} + (\kappa - 3)\sigma_{y_1 y_1} \right] \\ \varepsilon_{y_1 y_1}(x_1, y_1) &= \frac{\partial v_1}{\partial y_1} = \frac{1}{8\mu(x_1, y_1)} \left[(\kappa - 3)\sigma_{x_1 x_1} + (\kappa + 1)\sigma_{y_1 y_1} \right] \\ \varepsilon_{x_1 y_1}(x_1, y_1) &= \frac{1}{2} \left(\frac{\partial u_1}{\partial y_1} + \frac{\partial v_1}{\partial x_1} \right) = \frac{1}{2\mu(x_1, y_1)} \tau_{x_1 y_1}\end{aligned}\quad (32)$$

where κ is defined as,

$$\begin{aligned}\kappa &= 3 - 4\nu \dots\dots \text{for plane strain} \\ \kappa &= \frac{3 - \nu}{1 + \nu} \dots\dots \text{for plane stress}\end{aligned}\quad (33)$$

and the compatibility equation is defined as:

$$\frac{\partial^2 \epsilon_{x_1 x_1}}{\partial x_1^2} + \frac{\partial^2 \epsilon_{y_1 y_1}}{\partial y_1^2} - 2 \frac{\partial^2 \epsilon_{x_1 y_1}}{\partial x_1 \partial y_1} = 0 \quad (34)$$

From the compatibility equation the following fourth order governing equation for $U(x_1, y_1)$ is obtained,

$$\begin{aligned}\nabla^4 U(x_1, y_1) - 2\delta \frac{\partial}{\partial y_1} (\nabla^2 U(x_1, y_1)) - 2\beta \frac{\partial}{\partial x_1} (\nabla^2 U(x_1, y_1)) + \\ \frac{8\beta\delta}{1 + \kappa} \frac{\partial^2 U(x_1, y_1)}{\partial x_1 \partial y_1} + \beta^2 \left(\frac{\kappa - 3}{1 + \kappa} \frac{\partial^2 U(x_1, y_1)}{\partial y_1^2} + \frac{\partial^2 U(x_1, y_1)}{\partial x_1^2} \right) + \\ \delta^2 \left(\frac{\partial^2 U(x_1, y_1)}{\partial y_1^2} + \frac{\kappa - 3}{1 + \kappa} \frac{\partial^2 U(x_1, y_1)}{\partial x_1^2} \right) = 0\end{aligned}\quad (35)$$

where

$$\nabla = \left(\frac{\partial^2}{\partial x_1^2} + \frac{\partial^2}{\partial y_1^2} \right) \quad (36)$$

Defining the Fourier transform as follows,

$$V(\alpha, y_1) = \int_{-\infty}^{\infty} U(x_1, y_1) e^{-i\alpha x_1} dx_1 \quad (37)$$

and applying equation (37) to (35), the following characteristic equation is obtained,

$$\begin{aligned}n^4 - 2\delta n^3 + \left(\beta^2 \frac{\kappa_2 - 3}{\kappa_2 + 1} + \delta^2 - 2\alpha(i\beta + \alpha) \right) n^2 + \alpha\delta \left(\frac{8\beta}{\kappa_2 + 1} i + 2\alpha \right) n \\ + \alpha^2 \left(\alpha^2 + \delta^2 \frac{3 - \kappa_2}{\kappa_2 + 1} + \beta(2i\alpha - \beta) \right) = 0\end{aligned}\quad (38)$$

the roots of which are:

$$\begin{aligned}
 n_1 &= \frac{1}{2} \left(\delta + \beta \sqrt{\frac{3-\kappa}{\kappa+1}} \right) - \frac{1}{2} \sqrt{\left(\delta + \beta \sqrt{\frac{3-\kappa}{\kappa+1}} \right)^2 + 4(\alpha^2 + i\alpha \left(\beta - \delta \sqrt{\frac{3-\kappa}{\kappa+1}} \right))} \\
 n_2 &= \frac{1}{2} \left(\delta - \beta \sqrt{\frac{3-\kappa}{\kappa+1}} \right) - \frac{1}{2} \sqrt{\left(\delta - \beta \sqrt{\frac{3-\kappa}{\kappa+1}} \right)^2 + 4(\alpha^2 + i\alpha \left(\beta + \delta \sqrt{\frac{3-\kappa}{\kappa+1}} \right))} \\
 n_3 &= \frac{1}{2} \left(\delta + \beta \sqrt{\frac{3-\kappa}{\kappa+1}} \right) + \frac{1}{2} \sqrt{\left(\delta + \beta \sqrt{\frac{3-\kappa}{\kappa+1}} \right)^2 + 4(\alpha^2 + i\alpha \left(\beta - \delta \sqrt{\frac{3-\kappa}{\kappa+1}} \right))} \\
 n_4 &= \frac{1}{2} \left(\delta - \beta \sqrt{\frac{3-\kappa}{\kappa+1}} \right) + \frac{1}{2} \sqrt{\left(\delta - \beta \sqrt{\frac{3-\kappa}{\kappa+1}} \right)^2 + 4(\alpha^2 + i\alpha \left(\beta + \delta \sqrt{\frac{3-\kappa}{\kappa+1}} \right))}
 \end{aligned} \tag{39}$$

The solution to the ODE becomes:

$$V(\alpha, y_1) = B_1(\alpha)e^{n_1 y_1} + B_2(\alpha)e^{n_2 y_1} + B_3(\alpha)e^{n_3 y_1} + B_4(\alpha)e^{n_4 y_1} \tag{40}$$

so that,

$$U(x_1, y_1) = \frac{1}{2\pi} \int_{-\infty}^{\infty} [B_1(\alpha)e^{n_1 y_1} + B_2(\alpha)e^{n_2 y_1} + B_3(\alpha)e^{n_3 y_1} + B_4(\alpha)e^{n_4 y_1}] e^{ix_1 \alpha} d\alpha \tag{41}$$

Bounded form of equation (41) can be obtained upon examination of the roots of the characteristic equations. The real part of n_1 and n_2 are negative while that of n_3 and n_4 are positive as α approaches infinity. Hence U_2 is defined for positive and negative y_1 as,

$$\begin{aligned}
 U_2(x_1, y_1) &= \frac{1}{2\pi} \int_{-\infty}^{\infty} (B_1 e^{n_1 y_1} + B_2 e^{n_2 y_1}) e^{ix_1 \alpha} d\alpha; \dots\dots\dots y_1 > 0 \\
 U_2(x_1, y_1) &= \frac{1}{2\pi} \int_{-\infty}^{\infty} (B_3 e^{n_3 y_1} + B_4 e^{n_4 y_1}) e^{ix_1 \alpha} d\alpha; \dots\dots\dots y_1 < 0
 \end{aligned} \tag{42}$$

Normal and shear stresses must be continuous at $y_1=0$. The continuity conditions can be represented by equation (31) as:

$$\begin{aligned}
 \frac{\partial U(x_1, 0^+)}{\partial y_1} &= \frac{\partial U(x_1, 0^-)}{\partial y_1} \\
 U(x_1, 0^+) &= U(x_1, 0^-)
 \end{aligned} \tag{43}$$

where, 0^+ is for $y_1 > 0$ and 0^- is for $y_1 < 0$. Using conditions (43) we can eliminate B_3 and B_4 :

$$\begin{aligned} B_3 &= \frac{n_4 - n_1}{n_4 - n_3} B_1 + \frac{n_4 - n_2}{n_4 - n_3} B_2 \\ B_4 &= \frac{n_1 - n_3}{n_4 - n_3} B_1 + \frac{n_2 - n_3}{n_4 - n_3} B_2 \end{aligned} \quad (44)$$

The remaining two unknowns can be expressed in terms of the auxiliary functions:

$$\begin{aligned} f_1(x_1) &= \frac{\partial}{\partial x_1} [u_1(x_1, 0^+) - u_1(x_1, 0^-)] \\ f_2(x_1) &= \frac{\partial}{\partial x_1} [v_1(x_1, 0^+) - v_1(x_1, 0^-)] \end{aligned} \quad (45)$$

The final expressions of the stresses are obtained using (31) and Hooke's law,

$$\begin{aligned} \sigma_{x_1 y_1}(x_1, y_1^+) &= \frac{1}{2\pi} \int_{-\infty}^{\infty} [n_1^2 \frac{F_1(\alpha)h_{22} - F_2(\alpha)h_{12}}{h_{11}h_{22} - h_{12}h_{21}} e^{n_1 y_1} \\ &+ n_2^2 \frac{-F_1(\alpha)h_{21} + F_2(\alpha)h_{11}}{h_{11}h_{22} - h_{12}h_{21}} e^{n_2 y_1}] e^{i x_1 \alpha} d\alpha \end{aligned} \quad (46)$$

$$\begin{aligned} \sigma_{y_1 y_1}(x_1, y_1^+) &= -\frac{1}{2\pi} \int_{-\infty}^{\infty} \alpha^2 [\frac{F_1(\alpha)h_{22} - F_2(\alpha)h_{12}}{h_{11}h_{22} - h_{12}h_{21}} e^{n_1 y_1} \\ &+ \frac{-F_1(\alpha)h_{21} + F_2(\alpha)h_{11}}{h_{11}h_{22} - h_{12}h_{21}} e^{n_2 y_1}] e^{i x_1 \alpha} d\alpha \end{aligned} \quad (47)$$

$$\begin{aligned} \tau_{x_1 y_1}(x_1, y_1^+) &= -\frac{i}{2\pi} \int_{-\infty}^{\infty} \alpha [n_1 \frac{F_1(\alpha)h_{22} - F_2(\alpha)h_{12}}{h_{11}h_{22} - h_{12}h_{21}} e^{n_1 y_1} \\ &+ n_2 \frac{-F_1(\alpha)h_{21} + F_2(\alpha)h_{11}}{h_{11}h_{22} - h_{12}h_{21}} e^{n_2 y_1}] e^{i x_1 \alpha} d\alpha \end{aligned} \quad (48)$$

where,

$$\begin{aligned}
 h_{11} &= \frac{\kappa + 1}{8\mu_0} (n_1 - n_3)(n_1 - n_4) \\
 h_{12} &= \frac{\kappa + 1}{8\mu_0} (n_2 - n_3)(n_2 - n_4) \\
 h_{21} &= \frac{i\alpha - \beta}{8\mu_0} (\alpha^2(1 + \kappa) - \delta^2(\kappa_2 - 3)) \left[\frac{(n_1 - n_3)(n_1 - n_4)}{(\delta - n_1)(\delta - n_3)(\delta - n_4)} \right] \\
 h_{22} &= \frac{i\alpha - \beta}{8\mu_0} (\alpha^2(1 + \kappa) - \delta^2(\kappa_2 - 3)) \left[\frac{(n_2 - n_3)(n_2 - n_4)}{(\delta - n_2)(\delta - n_3)(\delta - n_4)} \right] \\
 F_j(\alpha) &= \int_a^b f_j(t) e^{(\beta - i\alpha)t} dt \dots \dots j = 1, 2.
 \end{aligned} \tag{49}$$

The singular integral equations can be solved for the auxiliary functions using the boundary conditions:

$$\begin{aligned}
 - p_1(x_1) &= \lim_{y_1 \rightarrow 0} \sigma_{y_1, y_1}(x_1, y_1) \dots \dots a < x_1 < b \\
 - p_2(x_1) &= \lim_{y_1 \rightarrow 0} \tau_{x_1, y_1}(x_1, y_1) \dots \dots a < x_1 < b
 \end{aligned} \tag{50}$$

Equation (47) and (48) are rearranged as follows,

$$\begin{aligned}
 \sigma_{y_1, y_1}(x_1, y_1^+) &= -\frac{1}{2\pi} \int_{-\infty}^{\infty} \alpha^2 \left[\frac{h_{22} e^{n_1 y_1} - h_{21} e^{n_2 y_1}}{h_{11} h_{22} - h_{12} h_{21}} F_1(\alpha) \right. \\
 &\quad \left. + \frac{h_{11} e^{n_2 y_1} - h_{12} e^{n_1 y_1}}{h_{11} h_{22} - h_{12} h_{21}} F_2(\alpha) \right] e^{i x_1 \alpha} d\alpha
 \end{aligned} \tag{51}$$

$$\begin{aligned}
 \tau_{x_1, y_1}(x_1, y_1^+) &= -\frac{i}{2\pi} \int_{-\infty}^{\infty} \alpha \left[\frac{n_1 h_{22} e^{n_1 y_1} - n_2 h_{21} e^{n_2 y_1}}{h_{11} h_{22} - h_{12} h_{21}} F_1(\alpha) \right. \\
 &\quad \left. + \frac{n_2 h_{11} e^{n_2 y_1} - n_1 h_{12} e^{n_1 y_1}}{h_{11} h_{22} - h_{12} h_{21}} F_2(\alpha) \right] e^{i x_1 \alpha} d\alpha
 \end{aligned} \tag{52}$$

As α goes to infinity $n_1 \cong n_2$ so X_{ij} can be expressed as defined in equation (9):

$$\begin{aligned}
 X_{11} &= -\alpha^2 \left[\frac{h_{22} - h_{21}}{h_{11} h_{22} - h_{12} h_{21}} \right] & X_{12} &= -\alpha^2 \left[\frac{h_{11} - h_{12}}{h_{11} h_{22} - h_{12} h_{21}} \right] \\
 X_{21} &= -i\alpha \left[\frac{n_1 h_{22} - n_2 h_{21}}{h_{11} h_{22} - h_{12} h_{21}} \right] & X_{22} &= -i\alpha \left[\frac{n_2 h_{11} - n_1 h_{12}}{h_{11} h_{22} - h_{12} h_{21}} \right]
 \end{aligned} \tag{53}$$

the asymptotes of X_{ij} are found as:

$$\begin{aligned}
X_{11}(+\infty) &= \frac{\delta}{\alpha(1+\kappa)} & X_{11}(-\infty) &= \frac{\delta}{-\alpha(1+\kappa)} \\
X_{12}(+\infty) &= \frac{2i}{(1+\kappa)} + \frac{\beta}{\alpha(1+\kappa)} & X_{12}(-\infty) &= \frac{-2i}{(1+\kappa)} + \frac{\beta}{-\alpha(1+\kappa)} \\
X_{21}(+\infty) &= \frac{2i}{(1+\kappa)} + \frac{\beta}{\alpha(1+\kappa)} & X_{21}(-\infty) &= \frac{-2i}{(1+\kappa)} + \frac{\beta}{-\alpha(1+\kappa)} \\
X_{22}(+\infty) &= \frac{-\delta}{\alpha(1+\kappa)} & X_{22}(-\infty) &= \frac{-\delta}{-\alpha(1+\kappa)}
\end{aligned} \tag{54}$$

so that from (54) it is concluded that $d_{ij}^1, e_{ij}^1, c_{ij}^1$ and g_{ij}^1 described earlier in equations

(12) and (18) become,

$$\begin{aligned}
d_{12}^1 &= d_{21}^1 = \frac{2}{1+\kappa} \\
e_{11}^1 &= -e_{22}^1 = \frac{\delta}{1+\kappa} \\
e_{12}^1 &= e_{21}^1 = \frac{\beta}{1+\kappa} \\
c_{11}^1 &= c_{12}^1 = c_{21}^1 = c_{22}^1 = d_{11}^1 = d_{22}^1 = g_{11}^1 = g_{12}^1 = g_{21}^1 = g_{22}^1 = 0
\end{aligned} \tag{55}$$

Now substituting (53) and (55) into (22) and (23) the final singular integral equations are reached,

$$\begin{aligned}
-\frac{\kappa+1}{2\mu(x_1,0)} p_1(x_1) &= \frac{1}{\pi} \int_a^b \frac{f_2(t)}{t-x_1} dt + \frac{1}{\pi} \int_a^b k_{12}(x_1, t) f_2(t) dt \\
&\quad - \frac{1}{\pi} \int_a^b \frac{\beta}{2} Ci(U(t-x_1)) f_2(t) dt \\
&\quad + \frac{1}{\pi} \int_a^b k_{11}(x_1, t) f_1(t) dt - \frac{1}{\pi} \int_a^b \frac{\delta}{2} Ci(U(t-x_1)) f_1(t) dt
\end{aligned} \tag{56}$$

$$\begin{aligned}
-\frac{\kappa+1}{2\mu(x_1,0)} p_2(x_1) &= \frac{1}{\pi} \int_a^b \frac{f_1(t)}{t-x_1} dt + \frac{1}{\pi} \int_a^b k_{21}(x_1, t) f_1(t) dt \\
&\quad - \frac{1}{\pi} \int_a^b \frac{\beta}{2} Ci(U(t-x_1)) f_1(t) dt \\
&\quad + \frac{1}{\pi} \int_a^b k_{22}(x_1, t) f_2(t) dt + \frac{1}{\pi} \int_a^b \frac{\delta}{2} Ci(U(t-x_1)) f_2(t) dt
\end{aligned} \tag{57}$$

where,

$$\begin{aligned}
k_{11}(x_1, t) = & \frac{\kappa + 1}{4} \left\{ \int_0^\infty \{ [X_{11c} - X_{11}] i \sin(\alpha(t - x_1)) \} d\alpha \right. \\
& + \int_0^U \{ [X_{11} + X_{11c}] \cos(\alpha(t - x_1)) \} d\alpha \\
& \left. + \int_U^\infty \left\{ [X_{11} + X_{11c} - 2 \frac{\delta}{\alpha(1 + \kappa)}] \cos(\alpha(t - x_1)) \right\} d\alpha \right\}
\end{aligned} \tag{58}$$

$$\begin{aligned}
k_{12}(x_1, t) = & \frac{\kappa + 1}{4} \left\{ \int_0^\infty \left\{ [X_{12c} - X_{12} + \frac{4i}{1 + \kappa}] i \sin(\alpha(t - x_1)) \right\} d\alpha \right. \\
& + \int_0^U \{ [X_{12} + X_{12c}] \cos(\alpha(t - x_1)) \} d\alpha \\
& \left. + \int_U^\infty \left\{ [X_{11} + X_{11c} - 2 \frac{\beta}{\alpha(1 + \kappa)}] \cos(\alpha(t - x_1)) \right\} d\alpha \right\}
\end{aligned} \tag{59}$$

$$\begin{aligned}
k_{21}(x_1, t) = & \frac{\kappa + 1}{4} \left\{ \int_0^\infty \left\{ [X_{21c} - X_{21} + \frac{4i}{1 + \kappa}] i \sin(\alpha(t - x_1)) \right\} d\alpha \right. \\
& + \int_0^U \{ [X_{21} + X_{21c}] \cos(\alpha(t - x_1)) \} d\alpha \\
& \left. + \int_U^\infty \left\{ [X_{21} + X_{21c} - 2 \frac{\beta}{\alpha(1 + \kappa)}] \cos(\alpha(t - x_1)) \right\} d\alpha \right\}
\end{aligned} \tag{60}$$

$$\begin{aligned}
k_{22}(x_1, t) = & \frac{\kappa + 1}{4} \left\{ \int_0^\infty \{ [X_{22c} - X_{22}] i \sin(\alpha(t - x_1)) \} d\alpha \right. \\
& + \int_0^U \{ [X_{22} + X_{22c}] \cos(\alpha(t - x_1)) \} d\alpha \\
& \left. + \int_U^\infty \left\{ [X_{22} + X_{22c} + 2 \frac{\delta}{\alpha(1 + \kappa)}] \cos(\alpha(t - x_1)) \right\} d\alpha \right\}
\end{aligned} \tag{61}$$

The definitions for the stress intensity factors (SIF) and the strain energy release rate (SERR) can be found in Konda and Erdogan (1994). Applying the Lobatto-Chebyshev collocation integration technique, as in Binienda and Arnold (1995), to the system of singular integral equations (56) and (57), the normalized mode I SIF were produced and compared to that of Konda and Erdogan (1994) as summarized in Table I.

Multiple Crack Formulation

To formulate the multiple crack problem the total stresses of the system needs to be determined. The cracks are located along their local x_i axes, which are related by the following coordinate transformation:

$$\begin{aligned}
 x_i &= x_{i+1} \cos(\theta_{i+1} - \theta_i) - y_{i+1} \sin(\theta_{i+1} - \theta_i) \\
 y_i &= x_{i+1} \sin(\theta_{i+1} - \theta_i) + y_{i+1} \cos(\theta_{i+1} - \theta_i) \\
 x_{i+1} &= x_i \cos(\theta_{i+1} - \theta_i) + y_i \sin(\theta_{i+1} - \theta_i) \\
 y_{i+1} &= -x_i \sin(\theta_{i+1} - \theta_i) + y_i \cos(\theta_{i+1} - \theta_i) \\
 \theta_{i+1} &> \theta_i
 \end{aligned} \tag{62}$$

and the stresses are related through the Cauchy stress transformation tensor:

$$\begin{aligned}
 \begin{Bmatrix} \sigma_{x_i x_i} \\ \sigma_{y_i y_i} \\ \tau_{x_i y_i} \end{Bmatrix} &= \begin{bmatrix} m^2 & n^2 & -2mn \\ n^2 & m^2 & 2mn \\ mn & -mn & m^2 - n^2 \end{bmatrix} \begin{Bmatrix} \sigma_{x_{i+1} x_{i+1}} \\ \sigma_{y_{i+1} y_{i+1}} \\ \tau_{x_{i+1} y_{i+1}} \end{Bmatrix} \\
 \begin{Bmatrix} \sigma_{x_{i+1} x_{i+1}} \\ \sigma_{y_{i+1} y_{i+1}} \\ \tau_{x_{i+1} y_{i+1}} \end{Bmatrix} &= \begin{bmatrix} m^2 & n^2 & 2mn \\ n^2 & m^2 & -2mn \\ -mn & mn & m^2 - n^2 \end{bmatrix} \begin{Bmatrix} \sigma_{x_i x_i} \\ \sigma_{y_i y_i} \\ \tau_{x_i y_i} \end{Bmatrix} \\
 m &= \cos(\theta_{i+1} - \theta_i); n = \sin(\theta_{i+1} - \theta_i)
 \end{aligned} \tag{63}$$

The material constants are:

$$\begin{aligned}
 \beta_i &= \gamma \sin(\theta_i) \\
 \delta_i &= \gamma \cos(\theta_i)
 \end{aligned} \tag{64}$$

The stresses for each coordinate system are expressed as:

$$\begin{aligned}
 \sigma_{x_i x_i}(x_i, y_i^+) &= \frac{1}{2\pi} \int_{-\infty}^{\infty} \left[\frac{n_1^{(i)} h_{22}^{(i)} e^{n_1 y_i} - n_2^{(i)} h_{21}^{(i)} e^{n_2 y_i}}{h_{11}^{(i)} h_{22}^{(i)} - h_{12}^{(i)} h_{21}^{(i)}} F_1^{(i)}(\alpha) \right. \\
 &\quad \left. + \frac{n_2^{(i)} h_{11}^{(i)} e^{n_2 y_i} - n_1^{(i)} h_{12}^{(i)} e^{n_1 y_i}}{h_{11}^{(i)} h_{22}^{(i)} - h_{12}^{(i)} h_{21}^{(i)}} F_2^{(i)}(\alpha) \right] e^{ix\alpha} d\alpha
 \end{aligned} \tag{65}$$

$$\begin{aligned}\sigma_{y_i y_i}(x_i, y_i^+) &= -\frac{1}{2\pi} \int_{-\infty}^{\infty} \alpha^2 \left[\frac{h_{22}^{(i)} e^{n_1 y_i} - h_{21}^{(i)} e^{n_2 y_i}}{h_{11}^{(i)} h_{22}^{(i)} - h_{12}^{(i)} h_{21}^{(i)}} F_1(\alpha) \right. \\ &\quad \left. + \frac{h_{11}^{(i)} e^{n_2 y_i} - h_{12}^{(i)} e^{n_1 y_i}}{h_{11}^{(i)} h_{22}^{(i)} - h_{12}^{(i)} h_{21}^{(i)}} F_2(\alpha) \right] e^{ix_i \alpha} d\alpha\end{aligned}\quad (66)$$

$$\begin{aligned}\tau_{x_i y_i}(x_i, y_i^+) &= -\frac{i}{2\pi} \int_{-\infty}^{\infty} \alpha \left[\frac{n_1 h_{22}^{(i)} e^{n_1 y_i} - n_2 h_{21}^{(i)} e^{n_2 y_i}}{h_{11}^{(i)} h_{22}^{(i)} - h_{12}^{(i)} h_{21}^{(i)}} F_1(\alpha) \right. \\ &\quad \left. + \frac{n_2 h_{11}^{(i)} e^{n_2 y_i} - n_1 h_{12}^{(i)} e^{n_1 y_i}}{h_{11}^{(i)} h_{22}^{(i)} - h_{12}^{(i)} h_{21}^{(i)}} F_2(\alpha) \right] e^{ix_i \alpha} d\alpha\end{aligned}\quad (67)$$

$$\begin{aligned}\sigma_{x_i x_i}(x_i, y_i^-) &= \frac{1}{2\pi} \int_{-\infty}^{\infty} \left[\frac{n_3^2 N_{22}^{(i)} e^{n_3 y_i} - n_4^2 N_{21}^{(i)} e^{n_4 y_i}}{N_{11}^{(i)} N_{22}^{(i)} - N_{12}^{(i)} N_{21}^{(i)}} F_1(\alpha) \right. \\ &\quad \left. + \frac{n_4^2 N_{11}^{(i)} e^{n_4 y_i} - n_3^2 N_{12}^{(i)} e^{n_3 y_i}}{N_{11}^{(i)} N_{22}^{(i)} - N_{12}^{(i)} N_{21}^{(i)}} F_2(\alpha) \right] e^{ix_i \alpha} d\alpha\end{aligned}\quad (68)$$

$$\begin{aligned}\sigma_{y_i y_i}(x_i, y_i^-) &= -\frac{1}{2\pi} \int_{-\infty}^{\infty} \alpha^2 \left[\frac{N_{22}^{(i)} e^{n_3 y_i} - N_{21}^{(i)} e^{n_4 y_i}}{N_{11}^{(i)} N_{22}^{(i)} - N_{12}^{(i)} N_{21}^{(i)}} F_1(\alpha) \right. \\ &\quad \left. + \frac{N_{11}^{(i)} e^{n_4 y_i} - N_{12}^{(i)} e^{n_3 y_i}}{N_{11}^{(i)} N_{22}^{(i)} - N_{12}^{(i)} N_{21}^{(i)}} F_2(\alpha) \right] e^{ix_i \alpha} d\alpha\end{aligned}\quad (69)$$

$$\begin{aligned}\tau_{x_i y_i}(x_i, y_i^-) &= -\frac{i}{2\pi} \int_{-\infty}^{\infty} \alpha \left[\frac{n_3 N_{22}^{(i)} e^{n_3 y_i} - n_4 N_{21}^{(i)} e^{n_4 y_i}}{N_{11}^{(i)} N_{22}^{(i)} - N_{12}^{(i)} N_{21}^{(i)}} F_1(\alpha) \right. \\ &\quad \left. + \frac{n_4 N_{11}^{(i)} e^{n_4 y_i} - n_3 N_{12}^{(i)} e^{n_3 y_i}}{N_{11}^{(i)} N_{22}^{(i)} - N_{12}^{(i)} N_{21}^{(i)}} F_2(\alpha) \right] e^{ix_i \alpha} d\alpha\end{aligned}\quad (70)$$

where,

$$\begin{aligned}
N_{11}^{(i)} &= \frac{\kappa + 1}{8\mu_0} (n_1 - n_3)(n_3 - n_2) \\
N_{12}^{(i)} &= \frac{\kappa + 1}{8\mu_0} (n_4 - n_2)(n_1 - n_4) \\
N_{21}^{(i)} &= \frac{i\alpha - \beta}{8\mu_0} (\alpha^2(1 + \kappa_2) - \delta_i^2(\kappa - 3)) \left[\frac{(n_1 - n_3)(n_3 - n_2)}{(\delta_i - n_1)(\delta_i - n_2)(\delta_i - n_3)} \right] \\
N_{22}^{(i)} &= \frac{i\alpha - \beta}{8\mu_0} (\alpha^2(1 + \kappa_2) - \delta_i^2(\kappa - 3)) \left[\frac{(n_4 - n_2)(n_1 - n_4)}{(\delta_i - n_2)(\delta_i - n_1)(\delta_i - n_4)} \right]
\end{aligned} \tag{71}$$

and h_{ij} are as defined in (49) for the i^{th} crack. Assume that there are n cracks present, then the stresses for the i^{th} crack could be expressed as:

$$\begin{aligned}
{}_i\sigma_{y_i y_i}^T(x_i, y_i) &= \sigma_{y_i y_i}^i(x_i, y_i) + \sum_{j=i+1}^n \sigma_{y_j y_j}^j[x_j(x_i, y_i), y_j(x_i, y_i)] \\
{}_i\tau_{y_i y_i}^T(x_i, y_i) &= \tau_{y_i y_i}^i(x_i, y_i) + \sum_{j=i+1}^n \tau_{y_j y_j}^j[x_j(x_i, y_i), y_j(x_i, y_i)]
\end{aligned} \tag{72}$$

where $\sigma_{y_i y_i}^{(j)}, \tau_{x_i y_i}^{(j)}$ are found using (63) and they are evaluated as in (9) and (10) respectively. One must be careful when choosing the stress components for the positive y_i (y_i^+) and for the negative y_i (y_i^-). Thus the final singular integral equation could be expressed for the i^{th} crack as:

$$\begin{aligned}
i\left(-\frac{\kappa+1}{2\mu(x_i,0)} p_1^{(i)}(x_i)\right) &= \frac{1}{\pi} \int_{a_i}^{b_i} \frac{f_2^{(i)}(t_i)}{t_i - x_i} dt_i + \frac{1}{\pi} \int_{a_i}^{b_i} k_{12}^{(i)}(x_i, t_i) f_2^{(i)}(t_i) dt_i \\
&\quad - \frac{1}{\pi} \int_{a_i}^{b_i} \frac{\beta_i}{2} Ci(U_i(t_i - x_i)) f_2^{(i)}(t_i) dt_i \\
&\quad + \frac{1}{\pi} \int_{a_i}^{b_i} k_{11}^{(i)}(x_i, t_i) f_1^{(i)}(t_i) dt_i - \frac{1}{\pi} \int_{a_i}^{b_i} \frac{\delta_i}{2} Ci(U(t_i - x_i)) f_1^{(i)}(t_i) dt_i \\
&\quad + \sum_{j=i+1}^n \left\{ \frac{1}{\pi} \int_{a_j}^{b_j} \left[\frac{a_{11}^{(j)}(x_i^2 \sin^2 \theta - (t_j - x_i \cos \theta)^2)}{(x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)^2} \right. \right. \\
&\quad + \frac{c_{11}^{(j)} x_i \sin \theta ((t_j - x_i \cos \theta)^2 + x_i^2 \sin^2 \theta)}{(x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)^2} \\
&\quad + \frac{2b_{11}^{(j)} x_i \sin \theta (t_j - x_i \cos \theta)}{(x_i^2 \sin^2 \theta + \cos^2 \theta (t - x_i)^2)^2} \\
&\quad \left. + \frac{(t_j - x_i \cos \theta) d_{11}^{(j)} (x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)}{(x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)^2} \right] f_1^{(j)}(t_j) dt_j \\
&\quad + \frac{1}{\pi} \int_{a_j}^{b_j} k_{11}^{(j)}(x_i, t_j) f_1^{(j)}(t_j) dt_j \\
&\quad + \frac{1}{\pi} \int_{a_j}^{b_j} \left[\frac{a_{12}^{(j)}(x_i^2 \sin^2 \theta - (t_j - x_i \cos \theta)^2)}{(x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)^2} \right. \\
&\quad + \frac{c_{12}^{(j)} x_i \sin \theta ((t_j - x_i \cos \theta)^2 + x_i^2 \sin^2 \theta)}{(x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)^2} \\
&\quad + \frac{2b_{12}^{(j)} x_i \sin \theta (t_j - x_i \cos \theta)}{(x_i^2 \sin^2 \theta + \cos^2 \theta (t - x_i)^2)^2} \\
&\quad \left. + \frac{d_{12}^{(j)} (t_j - x_i \cos \theta) (x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)}{(x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)^2} \right] f_2^{(j)}(t_j) dt_j \\
&\quad + \frac{1}{\pi} \int_{a_j}^{b_j} k_{12}^{(j)}(x_i, t_j) f_2^{(j)}(t_j) dt_j \left. \right\} \tag{73}
\end{aligned}$$

$$\begin{aligned}
i\left(-\frac{\kappa+1}{2\mu(x_i,0)} p_2^{(i)}(x_i)\right) &= \frac{1}{\pi} \int_{a_i}^{b_i} \frac{f_1^{(i)}(t_i)}{t_i - x_i} dt_i + \frac{1}{\pi} \int_{a_i}^{b_i} k_{21}^{(i)}(x_i, t_i) f_1^{(i)}(t_i) dt_i \\
&\quad - \frac{1}{\pi} \int_{a_i}^{b_i} \frac{\beta_i}{2} Ci(U_i(t_i - x_i)) f_1^{(i)}(t_i) dt_i \\
&\quad + \frac{1}{\pi} \int_{a_i}^{b_i} k_{22}^{(i)}(x_i, t_i) f_2^{(i)}(t_i) dt_i - \frac{1}{\pi} \int_{a_i}^{b_i} \frac{\delta_i}{2} Ci(U(t_i - x_i)) f_2^{(i)}(t_i) dt_i \\
&\quad + \sum_{j=i+1}^n \left\{ \frac{1}{\pi} \int_{a_j}^{b_j} \frac{a_{21}^{(j)}(x_i^2 \sin^2 \theta - (t_j - x_i \cos \theta)^2)}{(x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)^2} \right. \\
&\quad + \frac{c_{21}^{(j)} x_i \sin \theta ((t_j - x_i \cos \theta)^2 + x_i^2 \sin^2 \theta)}{(x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)^2} \\
&\quad + \frac{2b_{21}^{(j)} x_i \sin \theta (t_j - x_i \cos \theta)}{(x_i^2 \sin^2 \theta + \cos^2 \theta (t - x_i)^2)^2} \\
&\quad + \left. \frac{(t_j - x_i \cos \theta) d_{21}^{(j)} (x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)}{(x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)^2} \right] f_1^{(j)}(t_j) dt_j \\
&\quad + \frac{1}{\pi} \int_{a_j}^{b_j} k_{21}^{(j)}(x_i, t_j) f_1^{(j)}(t_j) dt_j \\
&\quad + \frac{1}{\pi} \int_{a_j}^{b_j} \frac{a_{22}^{(j)}(x_i^2 \sin^2 \theta - (t_j - x_i \cos \theta)^2)}{(x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)^2} \\
&\quad + \frac{c_{22}^{(j)} x_i \sin \theta ((t_j - x_i \cos \theta)^2 + x_i^2 \sin^2 \theta)}{(x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)^2} \\
&\quad + \frac{2b_{22}^{(j)} x_i \sin \theta (t_j - x_i \cos \theta)}{(x_i^2 \sin^2 \theta + \cos^2 \theta (t - x_i)^2)^2} \\
&\quad + \left. \frac{d_{22}^{(j)} (t_j - x_i \cos \theta) (x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)}{(x_i^2 \sin^2 \theta + (t_j - x_i \cos \theta)^2)^2} \right] f_2^{(j)}(t_j) dt_j \\
&\quad + \frac{1}{\pi} \int_{a_j}^{b_j} k_{22}^{(j)}(x_i, t_j) f_2^{(j)}(t_j) dt_j \} \tag{74}
\end{aligned}$$

where the constants $a_{mn}^{(j)} \cdots d_{mn}^{(j)}$ and $k_{mn}^{(j)}$ are defined in the Appendix, the kernels $k_{mn}^{(i)}$

are defined as in (58) through (64) and $\theta = \theta_j - \theta_i$.

The above solution is reduced to the case of two collinear cracks embedded in the isotropic plate to demonstrate high accuracy of the results as shown in Table II.

Parametric Studies

In the following parametric studies the length of all cracks is chosen to be $2c = 2$. The infinite plate is subjected to normal stress along y global direction, $\sigma_{yy}=1$ psi. Cracks are located along their local x_i axes, which can be inclined with respect to the global x axis. All the geometrical dimensions are normalized with respect to c. The parametric studies are presented for the normalized mode-I and mode-II SIF, i.e., k_1/k_0 and k_2/k_0 , and normalized SERR, i.e., G_1/G_0 and G_2/G_0 , where $k_0 = \sigma_{yy} \sqrt{c}$ and $G_0 = \frac{8\mu_0 k_0^2}{\pi(\kappa+1)}$.

First study takes into consideration the problem of two collinear horizontal cracks. The same crack configuration was used to produce the results in Table II for homogeneous materials, see insert in Figure 3 or 4. Here we extended the material properties to the show transition from homogeneous material to FGM. The distance between the inner tips is denoted by r. Figures 3 and 4 show mode I normalized SIF and mode-I normalized SERR versus a normalized crack tip distance r/c . The curves are shown using the logarithmic scale for the crack distance variable.

It can be noticed that as the distance between the cracks becomes smaller the SIF and SERR become larger for every power of the exponential variation coefficient γ . Note, that the homogeneous case is represented by making the coefficient $\gamma = 0$. Both driving forces increase as γ increases for materials becoming more nonhomogeneous. The increase is especially significant for the crack tip distance less than 0.01.

The case of collinear inclined cracks at 30 degrees from the horizontal axis is shown in Figures 5 to 8. Mode-I SIF shown in Figure 5 has larger magnitudes for both the homogeneous and FGM materials than the corresponding Mode-II SIF shown in Figure 6. Both modes show increase of SIF for decreasing of the crack tip distance and for increasing of the coefficient γ . Figures 7 and 8 display mode-I and II SERR. Magnitudes of Mode-I SERR are almost three times larger than the corresponding mode-II SERR. Both SERR modes increase for decreasing of the crack tip distance r (same as SIF) and for decreasing of γ (opposite to SIF). It should be pointed out that the material stiffness at each crack tip dominates the results for SERR to the point of reversing the trend in comparison with SIF with respect to γ .

The cases when two cracks are located along two different local radial axes distance $d = 1$ from the origin is shown in the remaining figures. The location of the first crack is kept constant at 30 degrees while orientation of the second crack is changed from 45 to 90 degrees. Both SIF and SERR are shown for each crack tip versus the orientation angle of the second crack.

Figures 9 and 10 display mode-I and II SIF while Figures 11 and 12 represent both modes of SERR at the left crack tip of the stationary crack 1. It can be noticed that when crack 2 comes closer to crack 1, the tip a_1 is shielded and all driving force components are significantly reduced. Mode-II SIF has its maximum for the orientation angle of the second crack close to 70 degrees. By increasing γ higher magnitudes for mode-I SIF and lower magnitudes for mode-II SIF are produced.

Both modes of the SERR depend not only on square of the SIF but also on the material stiffness at the crack tip. This influence is especially shown in Figure 11 where

the homogeneous case produces the smallest SERR for angle 45 degrees similar to the corresponding SIF. However, homogeneous SERR curve becomes largest for higher angles, which is opposite to the corresponding SIF.

The opposite character of SIF and SERR is even better shown in Figures 13 to 16. Here the shielding effect does not exhibit itself. Both modes of SIF for the homogeneous material are smallest (see Figures 13 and 14 for mode-I and II SIF), while both components of SERR are largest (see Figures 15 and 16 for mode-I and II SERR), because of the crack tip material stiffness influence.

The results for the left crack tip of the second crack are shown in Figures 17 to 20. Mode-I SIF depends on the crack orientation and for homogeneous case is smallest. The negative values of the mode-I SIF should be interpreted as the crack closure and SERR for such case is zero.

Mode-II SIF at the tip of the second crack versus its orientation is shown in Figure 18. For the homogeneous case the maximum k_2 is at 45 degrees. In the cases of higher coefficient γ the maximum k_2 is shifted towards 60 degrees crack orientation. The magnitudes of SIF are larger for nonhomogeneous cases than for the homogeneous case when the orientation angles of the second crack are higher than 60 degree.

Mode-I of SERR monotonically decreases to almost zero at 75 degrees and at about 50 degrees does not depend on γ , see Figure 19. For 45-50 degrees the homogeneous case is the highest and for 50-90 is the smallest. Mode-II SERR is the highest for 45-90 degrees angle orientation and has its maximum at 45 degrees, see Figure 20. The shift of the maximum to 55 degrees can only be observed for $\gamma=1.0$.

Mode-I SIF for the right crack tip b_2 is very small for all the angles examined or it is negative (crack closure) for the angle more than 65 degrees for the homogeneous case and down to 50 degrees for FGM with $\gamma=1$. Mode-II SIF is shown in Figure 22. The maximum is moved to 60 degrees because of the influence of the crack below. The homogeneous material case is the smallest for all the angles of the crack orientation.

Mode-I SERR at the same crack tip is shown in Figure 23. Homogeneous case starts to be the highest at the orientation of 45 degrees and quickly goes to zero at 62 degrees. The FGM with the highest γ also goes to zero but at the smaller angle because the crack tip remains closed. Mode-II SERR is shown in Figure 24. All the curves have their maximum at 55 degrees. The highest SERR is for $\gamma = 1.0$ and the smallest for $\gamma = 0.25$ at the angle of 45 degrees. The homogeneous material produces the smallest SERR for the orientation close to 75 degrees.

All of the above parametric studies demonstrate that the effect of the material properties, crack orientation, location of the additional crack are interdependent and consequently produce behavior different than isotropic homogeneous materials. The model developed in this work can be used to study fracture problems in FGM and can be used to tailor the properties in order to reduce driving force components and effectively increase life of these materials.

Conclusions

Application of the general solution to the mixed boundary value problem was demonstrated to provide an elegant way of obtaining the fundamental solution for a crack embedded in an infinite nonhomogeneous plate. The fundamental solution was used to

address multiple crack problem. Parametric studies for the multiple cracks revealed, that both SIF and SERR highly depend on the crack geometrical parameters such as crack orientation, location, relative distance, etc., but they also depend on the power of the exponent describing the rate of change of the material elastic parameters, γ , and local stiffness of the material at each crack tip.

The results demonstrated that the driving forces can be amplified by the collinear crack orientation or they can be reduced by the shielding effect between cracks above or below. The character of the amplification or shielding remains similar for nonhomogeneous materials but in most cases higher than zero coefficient γ increases SIF and reduces SERR.

The well known one-to-one relation between SIF and SERR curves is not always valid for FGM, because SERR also depends on the material elastic constants. Hence, the SIF curves may have different character than SERR curves. The application of the driving forces to crack propagation criterion need to be further studied to determine which driving force (SIF or SERR) best correlates with appropriate experimental results. However, since SERR includes the influence of SIF and material stiffness at the tip it is recommended that total SERR is used for the driving force parameter for FGM.

Reference

Abramowitz, A., and Stegun, I. E., 1964, Handbook of Mathematical Functions, National Bureau of Standards.

Asish, G., Yoshinari, M., Ivar, R., and John, J. L., (eds.), 1997, Functionally Graded Materials, Ceramic Trans., vol. 76.

Binienda, W. K., and Arnold, S. M., 1995, "Driving Force Analysis in an Infinite Anisotropic Plate with Multiple Crack Interactions," International Journal of Fracture, Vol. 71, pp. 213-245.

Delale, F., and Erdogan, F., 1983, "The Crack Problem for a Non-Homogeneous Plan," Journal of Applied Mechanics, Vol. 50, pp. 609-614.

Delale, F., and Erdogan, F., 1988, "On the Mechanical Modeling of the Interfacial Region in Bonded Half-Planes," Journal of Applied Mechanics, Vol. 55, pp. 317-324.

Erdogan, F., 1962, "On the Stress Distribution in Plates with Collinear Cuts Under Arbitrary Loads," Proceedings of the Fourth U.S. National Congress of Applied Mechanics, Vol. 1, ASME, New York, pp. 547-553.

Hirano, T., Yamada, T., Teraki, J., Niino, M., and Kumakawa, A., 1988, "A Study on Functionally Gradient Material Design System for a Thrust Chamber," Proc. 16th Int. Symp. On Space Technology and Science, Sapporo, Japan.

Hirano, T., and Yamada, T., 1988, "Multi-Paradigm Expert System Architecture Based Upon the Inverse Design Concept," Int. Workshop on Artificial Intelligence for Industrial Applications, Hitachi, Japan.

Holt J. B., Mitsue, K., Toshio, H., and Zuhir, A. M., (eds.), 1993, Functionally Graded Materials, Ceramic Trans., vol. 34, The American Ceramic Society, Westerville, Ohio.

Horii, H., and Nemat-Nasser, S., 1985, "Elastic Fields of Interacting Inhomogeneities," *Int. J. Solids Structure*, Vol. 21, no. 7, pp. 731-745.

Kawasaki, A., and Watanabe, R., 1990, "Fabrication of Sintered Functionally Gradient Material by Powder Spray Forming Process," FGM-90, Proc. of the 1st Int. Symp. On FGM from, Sendai, Japan.

Konda, N., and Erdogan, F., 1994, "The Mixed Mode Crack Problem in a Non-Homogeneous Elastic Medium," *Engineering Fracture Mechanics*, Vol. 47, No. 4, pp. 533-545.

Niino, M., and Maeda, S., 1990, "Recent Development Status of Functionally Gradient Materials," *I. S. I. J. Int.* 30, pp. 699-703.

Pindera, M. J., Abodi, J. and Arnold, S. M.(1997). "The Effect of Microstructure on the Response of Functionally Graded Thermal Barrier Coatings." *Proc. Of the HITEMP Review*, Vol. II: Advanced Alloys and MMC.

Table I Verification of the Solution.

$c\gamma$	Konda and Erdogan (1994) $k_1(a)/\sqrt{c}$	Present Study $k_1(a)/\sqrt{c}$	Konda and Erdogan (1994) $k_2(a)/\sqrt{c}$	Present Study $k_2(a)/\sqrt{c}$
0.25	1.036	1.036	0.065	0.062
0.50	1.101	1.101	0.129	0.122
1.0	1.258	1.260	0.263	0.243

$c=(b-a)/2$

Table II Two Collinear Cracks In Isotropic Plate

$\frac{r_d}{c}$	From literature				Present Method	
	Horri and Nemat-Nasser (1985)		Erdogan (1962)			
	Inner	Outer	Inner	Outer	Inner	Outer
0.22	---	---	1.45387	1.11741	1.45736	1.11786
0.50	1.2289	1.0811	1.22894	1.08107	1.22894	1.08107
0.857	1.1333	1.0579	1.13326	1.05786	1.13329	1.05787

APPENDIX

$$a_{11}^{(1)} = \operatorname{Re} \left[\frac{4 E^{2I\theta} \alpha \operatorname{Sinh}[a] \sqrt{\frac{1}{1+\kappa_2}}}{(\beta - I\delta) \sqrt{3 - \kappa_2}} \right]$$

$$a_{12}^{(1)} = \operatorname{Re} \left[-\frac{4 I E^{2I\theta} \alpha \operatorname{Sinh}[a] \sqrt{\frac{1}{1+\kappa_2}}}{(\beta - I\delta) \sqrt{3 - \kappa_2}} \right]$$

$$a_{21}^{(1)} = \operatorname{Re} \left[\frac{4 E^{2I\theta} \alpha \operatorname{Sinh}[a] \sqrt{\frac{1}{1+\kappa_2}}}{(-I\beta - \delta) \sqrt{3 - \kappa_2}} \right]$$

$$a_{22}^{(1)} = \operatorname{Re} \left[\frac{4 E^{2I\theta} \alpha \operatorname{Sinh}[a] \sqrt{\frac{1}{1+\kappa_2}}}{(\beta - I\delta) \sqrt{3 - \kappa_2}} \right]$$

$$b_{11}^{(1)} = \operatorname{Im} \left[\frac{4 E^{2I\theta} \alpha \operatorname{Sinh}[a] \sqrt{\frac{1}{1+\kappa_2}}}{(\beta - I\delta) \sqrt{3 - \kappa_2}} \right]$$

$$b_{12}^{(1)} = \operatorname{Im} \left[-\frac{4 I E^{2I\theta} \alpha \operatorname{Sinh}[a] \sqrt{\frac{1}{1+\kappa_2}}}{(\beta - I\delta) \sqrt{3 - \kappa_2}} \right]$$

$$b_{21}^{(1)} = \operatorname{Im} \left[\frac{4 E^{2I\theta} \alpha \operatorname{Sinh}[a] \sqrt{\frac{1}{1+\kappa_2}}}{(-I\beta - \delta) \sqrt{3 - \kappa_2}} \right]$$

$$b_{22}^{(1)} = \operatorname{Im} \left[\frac{4 E^{2I\theta} \alpha \operatorname{Sinh}[a] \sqrt{\frac{1}{1+\kappa_2}}}{(\beta - I\delta) \sqrt{3 - \kappa_2}} \right]$$

$$c_{11}^{(1)} = \operatorname{Re} \left[\frac{2 (-I \cos[\theta] + \sin[\theta]) \sqrt{\frac{1}{1+\kappa_2}} \left(E^{-I\theta} \operatorname{Sinh}[a] - 2 \operatorname{Cosh}[a] \sin[\theta] \sqrt{-1 + \frac{4}{1+\kappa_2}} \right)}{\sqrt{3 - \kappa_2}} \right]$$

$$c_{12}^{(1)} = \operatorname{Re} \left[2 I \left(\frac{(2 I \sin[\theta]^2 + \sin[2\theta]) \operatorname{Sinh}[a] \sqrt{\frac{1}{1+\kappa_2}}}{\sqrt{3 - \kappa_2}} + \frac{\operatorname{Cosh}[a]}{1 + \kappa_2} \right) \right]$$

$$c_{21}^{(i)} = \operatorname{Re} \left[\frac{2 I E^{2I\theta} \operatorname{Cosh}[a]}{1 + \kappa_2} \right]$$

$$c_{22}^{(i)} = \operatorname{Re} \left[\frac{2 I E^{2I\theta} \operatorname{Sinh}[a] \sqrt{\frac{1}{1+\kappa_2}}}{\sqrt{3-\kappa_2}} \right]$$

$$d_{11}^{(i)} = \operatorname{Im} \left[\frac{2 (-I \operatorname{Cos}[\theta] + \operatorname{Sin}[\theta]) \sqrt{\frac{1}{1+\kappa_2}} \left(E^{-I\theta} \operatorname{Sinh}[a] - 2 \operatorname{Cosh}[a] \operatorname{Sin}[\theta] \sqrt{-1 + \frac{4}{1+\kappa_2}} \right)}{\sqrt{3-\kappa_2}} \right]$$

$$d_{12}^{(i)} = \operatorname{Im} \left[2 I \left(\frac{(2 I \operatorname{Sin}[\theta]^2 + \operatorname{Sin}[2\theta]) \operatorname{Sinh}[a] \sqrt{\frac{1}{1+\kappa_2}}}{\sqrt{3-\kappa_2}} + \frac{\operatorname{Cosh}[a]}{1+\kappa_2} \right) \right]$$

$$d_{21}^{(i)} = \operatorname{Im} \left[\frac{2 I E^{2I\theta} \operatorname{Cosh}[a]}{1 + \kappa_2} \right]$$

$$d_{22}^{(i)} = \operatorname{Im} \left[\frac{2 I E^{2I\theta} \operatorname{Sinh}[a] \sqrt{\frac{1}{1+\kappa_2}}}{\sqrt{3-\kappa_2}} \right]$$

$$a_{11}^{(i,1)} = \operatorname{Re} \left[\frac{4 E^{2I\theta} \alpha \operatorname{Sinh}[b] \sqrt{\frac{1}{1+\kappa_2}}}{(\beta + I \delta) \sqrt{3-\kappa_2}} \right]$$

$$a_{12}^{(i,1)} = \operatorname{Re} \left[\frac{4 I E^{2I\theta} \alpha \operatorname{Sinh}[b] \sqrt{\frac{1}{1+\kappa_2}}}{(\beta + I \delta) \sqrt{3-\kappa_2}} \right]$$

$$a_{21}^{(i,1)} = \operatorname{Re} \left[\frac{4 E^{2I\theta} \alpha \operatorname{Sinh}[b] \sqrt{\frac{1}{1+\kappa_2}}}{(I \beta - \delta) \sqrt{3-\kappa_2}} \right]$$

$$a_{22}^{(i,1)} = \operatorname{Re} \left[\frac{4 E^{2I\theta} \alpha \operatorname{Sinh}[b] \sqrt{\frac{1}{1+\kappa_2}}}{(\beta + I \delta) \sqrt{3-\kappa_2}} \right]$$

$$b_{11}^{(i,1)} = \operatorname{Im} \left[\frac{4 E^{2I\theta} \alpha \operatorname{Sinh}[b] \sqrt{\frac{1}{1+\kappa_2}}}{(\beta + I \delta) \sqrt{3-\kappa_2}} \right]$$

$$b_{12}^{(i,1)} = \operatorname{Im} \left[\frac{4 I E^{2I\theta} \alpha \operatorname{Sinh}[b] \sqrt{\frac{1}{1+\kappa_2}}}{(\beta + I \delta) \sqrt{3-\kappa_2}} \right]$$

$$b_{21}^{(i+1)} = \text{Im} \left[\frac{4 E^{2I\theta} \alpha \text{Sinh}[b] \sqrt{\frac{1}{1+\kappa_2}}}{(I\beta - \delta) \sqrt{3 - \kappa_2}} \right]$$

$$b_{22}^{(i+1)} = \text{Im} \left[\frac{4 E^{2I\theta} \alpha \text{Sinh}[b] \sqrt{\frac{1}{1+\kappa_2}}}{(\beta + I\delta) \sqrt{3 - \kappa_2}} \right]$$

$$c_{11}^{(i+1)} = \text{Re} \left[\frac{4 \text{Cosh}[b] \text{Sin}[\theta] (-I \text{Cos}[\theta] + \text{Sin}[\theta])}{1 + \kappa_2} + \frac{2 I \text{Sinh}[b] \sqrt{\left(\frac{3-\kappa_2}{1+\kappa_2}\right)}}{-3 + \kappa_2} \right]$$

$$c_{12}^{(i+1)} = \text{Re} \left[-\frac{2 (-1 + E^{2I\theta}) \text{Sinh}[b] \sqrt{\frac{1}{1+\kappa_2}}}{\sqrt{3 - \kappa_2}} + \frac{2 I \text{Cosh}[b]}{1 + \kappa_2} \right]$$

$$c_{21}^{(i+1)} = \text{Re} \left[\frac{2 I E^{2I\theta} \text{Cosh}[b]}{1 + \kappa_2} \right]$$

$$c_{22}^{(i+1)} = \text{Re} \left[\frac{2 I E^{2I\theta} \text{Sinh}[b] \sqrt{\frac{1}{1+\kappa_2}}}{\sqrt{3 - \kappa_2}} \right]$$

$$d_{11}^{(i+1)} = \text{Im} \left[\frac{4 \text{Cosh}[b] \text{Sin}[\theta] (-I \text{Cos}[\theta] + \text{Sin}[\theta])}{1 + \kappa_2} + \frac{2 I \text{Sinh}[b] \sqrt{\left(\frac{3-\kappa_2}{1+\kappa_2}\right)}}{-3 + \kappa_2} \right]$$

$$d_{12}^{(i+1)} = \text{Im} \left[-\frac{2 (-1 + E^{2I\theta}) \text{Sinh}[b] \sqrt{\frac{1}{1+\kappa_2}}}{\sqrt{3 - \kappa_2}} + \frac{2 I \text{Cosh}[b]}{1 + \kappa_2} \right]$$

$$d_{21}^{(i+1)} = \text{Im} \left[\frac{2 I E^{2I\theta} \text{Cosh}[b]}{1 + \kappa_2} \right]$$

$$d_{22}^{(i+1)} = \text{Im} \left[\frac{2 I E^{2I\theta} \text{Sinh}[b] \sqrt{\frac{1}{1+\kappa_2}}}{\sqrt{3 - \kappa_2}} \right]$$

where,

$$\theta = \theta_{i+1} - \theta_i$$

$$a = -\frac{1}{2} x_i \text{Sin}[\theta] (\beta - i \delta) \sqrt{\frac{3 - \kappa_2}{\kappa_2 + 1}}$$

$$b = \frac{1}{2} x_{i+1} \text{Sin}[\theta] (\beta + i \delta) \sqrt{\frac{3 - \kappa_2}{\kappa_2 + 1}}$$

and,

$$k_{11}^{(i)} = \frac{\kappa + 1}{4 \text{Exp}[\beta x_i]} \left(\left(x_{112tc} + x_{112t} - 2 * \left(a_{11}^{(i)} + c_{11}^{(i)} \right) * \text{Exp}[-\alpha x_i \text{Sin}[\theta]] \right) \text{Cos}[\alpha (t_{i+1} - x_i \text{Cos}[\theta])] + \right. \\ \left. i \left(x_{112tc} - x_{112t} + 2 i \left(b_{11}^{(i)} + d_{11}^{(i)} \right) * \text{Exp}[-\alpha x_i \text{Sin}[\theta]] \right) \text{Sin}[\alpha (t_{i+1} - x_i \text{Cos}[\theta])] \right)$$

$$k_{12}^{(i)} = \frac{\kappa_2 + 1}{4 \text{Exp}[\beta x_i]} \left(\left(x_{122tc} + x_{122t} - 2 * \left(a_{12}^{(i)} + c_{12}^{(i)} \right) * \text{Exp}[-\alpha x_i \text{Sin}[\theta]] \right) \text{Cos}[\alpha (t_{i+1} - x_i \text{Cos}[\theta])] + \right. \\ \left. i \left(x_{122tc} - x_{122t} + 2 i \left(b_{12}^{(i)} + d_{12}^{(i)} \right) * \text{Exp}[-\alpha x_i \text{Sin}[\theta]] \right) \text{Sin}[\alpha (t_{i+1} - x_i \text{Cos}[\theta])] \right)$$

$$k_{21}^{(i)} = \frac{\kappa_2 + 1}{4 \text{Exp}[\beta x_i]} \left(\left(x_{212tc} + x_{212t} - 2 * \left(a_{21}^{(i)} + c_{21}^{(i)} \right) * \text{Exp}[-\alpha x_i \text{Sin}[\theta]] \right) \text{Cos}[\alpha (t_{i+1} - x_i \text{Cos}[\theta])] + \right. \\ \left. i \left(x_{212tc} - x_{212t} + 2 i \left(b_{21}^{(i)} + d_{21}^{(i)} \right) * \text{Exp}[-\alpha x_i \text{Sin}[\theta]] \right) \text{Sin}[\alpha (t_{i+1} - x_i \text{Cos}[\theta])] \right)$$

$$k_{22}^{(i)} = \frac{\kappa_2 + 1}{4 \text{Exp}[\beta x_i]} \left(\left(x_{222tc} + x_{222t} - 2 * \left(a_{22}^{(i)} + c_{22}^{(i)} \right) * \text{Exp}[-\alpha x_i \text{Sin}[\theta]] \right) \text{Cos}[\alpha (t_{i+1} - x_i \text{Cos}[\theta])] + \right. \\ \left. i \left(x_{222tc} - x_{222t} + 2 i \left(b_{22}^{(i)} + d_{22}^{(i)} \right) * \text{Exp}[-\alpha x_i \text{Sin}[\theta]] \right) \text{Sin}[\alpha (t_{i+1} - x_i \text{Cos}[\theta])] \right)$$

$$k_{11}^{(i+1)} = \frac{\kappa_2 + 1}{4 \text{Exp}[\beta x_{i+1}]} \left(\left(x_{111tc} + x_{111t} - 2 * \left(a_{11}^{(i+1)} + c_{11}^{(i+1)} \right) * \text{Exp}[-\alpha x_{i+1} \text{Sin}[\theta]] \right) \text{Cos}[\alpha (t_i - x_{i+1} \text{Cos}[\theta])] + \right. \\ \left. i \left(x_{111tc} - x_{111t} + 2 i \left(b_{11}^{(i+1)} + d_{11}^{(i+1)} \right) * \text{Exp}[-\alpha x_{i+1} \text{Sin}[\theta]] \right) \text{Sin}[\alpha (t_i - x_{i+1} \text{Cos}[\theta])] \right)$$

$$k_{12}^{(i+1)} = \frac{\kappa_2 + 1}{4 \text{Exp}[\beta x_{i+1}]} \left(\left(x_{121tc} + x_{121t} - 2 * \left(a_{12}^{(i+1)} + c_{12}^{(i+1)} \right) * \text{Exp}[-\alpha x_{i+1} \text{Sin}[\theta]] \right) \text{Cos}[\alpha (t_i - x_{i+1} \text{Cos}[\theta])] + \right. \\ \left. i \left(x_{121tc} - x_{121t} + 2 i \left(b_{12}^{(i+1)} + d_{12}^{(i+1)} \right) * \text{Exp}[-\alpha x_{i+1} \text{Sin}[\theta]] \right) \text{Sin}[\alpha (t_i - x_{i+1} \text{Cos}[\theta])] \right)$$

$$k_{21}^{(i+1)} = \frac{\kappa_2 + 1}{4 \text{Exp}[\beta x_{i+1}]} \left(\left(x_{211tc} + x_{211t} - 2 * \left(a_{21}^{(i+1)} + c_{21}^{(i+1)} \right) * \text{Exp}[-\alpha x_{i+1} \text{Sin}[\theta]] \right) \text{Cos}[\alpha (t_i - x_{i+1} \text{Cos}[\theta])] + \right. \\ \left. i \left(x_{211tc} - x_{211t} + 2 i \left(b_{21}^{(i+1)} + d_{21}^{(i+1)} \right) * \text{Exp}[-\alpha x_{i+1} \text{Sin}[\theta]] \right) \text{Sin}[\alpha (t_i - x_{i+1} \text{Cos}[\theta])] \right)$$

$$k_{22}^{(i+1)} = \frac{\kappa_2 + 1}{4 \text{Exp}[\beta x_{i+1}]} \left(\left(x_{221tc} + x_{221t} - 2 * \left(a_{22}^{(i+1)} + c_{22}^{(i+1)} \right) * \text{Exp}[-\alpha x_{i+1} \text{Sin}[\theta]] \right) \text{Cos}[\alpha (t_i - x_{i+1} \text{Cos}[\theta])] + \right. \\ \left. i \left(x_{221tc} - x_{221t} + 2 i \left(b_{22}^{(i+1)} + d_{22}^{(i+1)} \right) * \text{Exp}[-\alpha x_{i+1} \text{Sin}[\theta]] \right) \text{Sin}[\alpha (t_i - x_{i+1} \text{Cos}[\theta])] \right)$$

where,

$$x_{112t} = \text{Sin}[\theta]^2 \left(\frac{n_3^2 N_{22} e^{-n_3 x_1 \text{Sin}[\theta]} - n_4^2 N_{21} e^{-n_4 x_1 \text{Sin}[\theta]}}{N_{11} N_{22} - N_{12} N_{21}} \right) + \text{Cos}[\theta]^2 \left(-\alpha^2 \frac{N_{22} e^{-n_3 x_1 \text{Sin}[\theta]} - N_{21} e^{-n_4 x_1 \text{Sin}[\theta]}}{N_{11} N_{22} - N_{12} N_{21}} \right) +$$

$$2 \text{Sin}[\theta] \text{Cos}[\theta] \left(-i \alpha \frac{n_3 N_{22} e^{-n_3 x_1 \text{Sin}[\theta]} - n_4 N_{21} e^{-n_4 x_1 \text{Sin}[\theta]}}{N_{11} N_{22} - N_{12} N_{21}} \right)$$

$$x_{122t} = \text{Sin}[\theta]^2 \left(\frac{n_4^2 N_{11} e^{-n_4 x_1 \text{Sin}[\theta]} - n_3^2 N_{12} e^{-n_3 x_1 \text{Sin}[\theta]}}{N_{11} N_{22} - N_{12} N_{21}} \right) + \text{Cos}[\theta]^2 \left(-\alpha^2 \frac{N_{11} e^{-n_4 x_1 \text{Sin}[\theta]} - N_{12} e^{-n_3 x_1 \text{Sin}[\theta]}}{N_{11} N_{22} - N_{12} N_{21}} \right) +$$

$$2 \text{Sin}[\theta] \text{Cos}[\theta] \left(-i \alpha \frac{n_4 N_{11} e^{-n_4 x_1 \text{Sin}[\theta]} - n_3 N_{12} e^{-n_3 x_1 \text{Sin}[\theta]}}{N_{11} N_{22} - N_{12} N_{21}} \right)$$

$$x_{212t} = \text{Sin}[\theta] \text{Cos}[\theta] \left(\frac{n_3^2 N_{22} e^{-n_3 x_1 \text{Sin}[\theta]} - n_4^2 N_{21} e^{-n_4 x_1 \text{Sin}[\theta]}}{N_{11} N_{22} - N_{12} N_{21}} \right) -$$

$$\text{Sin}[\theta] \text{Cos}[\theta] \left(-\alpha^2 \frac{N_{22} e^{-n_3 x_1 \text{Sin}[\theta]} - N_{21} e^{-n_4 x_1 \text{Sin}[\theta]}}{N_{11} N_{22} - N_{12} N_{21}} \right) +$$

$$(\text{Cos}[\theta]^2 - \text{Sin}[\theta]^2) \left(-i \alpha \frac{n_3 N_{22} e^{-n_3 x_1 \text{Sin}[\theta]} - n_4 N_{21} e^{-n_4 x_1 \text{Sin}[\theta]}}{N_{11} N_{22} - N_{12} N_{21}} \right)$$

$$x_{222t} = \text{Sin}[\theta] \text{Cos}[\theta] \left(\frac{n_4^2 N_{11} e^{-n_4 x_1 \text{Sin}[\theta]} - n_3^2 N_{12} e^{-n_3 x_1 \text{Sin}[\theta]}}{N_{11} N_{22} - N_{12} N_{21}} \right) -$$

$$\text{Sin}[\theta] \text{Cos}[\theta] \left(-\alpha^2 \frac{N_{11} e^{-n_4 x_1 \text{Sin}[\theta]} - N_{12} e^{-n_3 x_1 \text{Sin}[\theta]}}{N_{11} N_{22} - N_{12} N_{21}} \right) +$$

$$(\text{Cos}[\theta]^2 - \text{Sin}[\theta]^2) \left(-i \alpha \frac{n_4 N_{11} e^{-n_4 x_1 \text{Sin}[\theta]} - n_3 N_{12} e^{-n_3 x_1 \text{Sin}[\theta]}}{N_{11} N_{22} - N_{12} N_{21}} \right)$$

$$x_{111t} = \text{Sin}[\theta]^2 \left(\frac{n_1^2 h_{22} e^{n_1 x_{1+1} \text{Sin}[\theta]} - n_2^2 h_{21} e^{n_2 x_{1+1} \text{Sin}[\theta]}}{h_{11} h_{22} - h_{12} h_{21}} \right) + \text{Cos}[\theta]^2 \left(-\alpha^2 \frac{h_{22} e^{n_1 x_{1+1} \text{Sin}[\theta]} - h_{21} e^{n_2 x_{1+1} \text{Sin}[\theta]}}{h_{11} h_{22} - h_{12} h_{21}} \right) -$$

$$2 \text{Sin}[\theta] \text{Cos}[\theta] \left(-i \alpha \frac{n_1 h_{22} e^{n_1 x_{1+1} \text{Sin}[\theta]} - n_2 h_{21} e^{n_2 x_{1+1} \text{Sin}[\theta]}}{h_{11} h_{22} - h_{12} h_{21}} \right)$$

$$x_{121t} = \text{Sin}[\theta]^2 \left(\frac{n_2^2 h_{11} e^{n_2 x_{1+1} \text{Sin}[\theta]} - n_1^2 h_{12} e^{n_1 x_{1+1} \text{Sin}[\theta]}}{h_{11} h_{22} - h_{12} h_{21}} \right) + \text{Cos}[\theta]^2 \left(-\alpha^2 \frac{h_{11} e^{n_2 x_{1+1} \text{Sin}[\theta]} - h_{12} e^{n_1 x_{1+1} \text{Sin}[\theta]}}{h_{11} h_{22} - h_{12} h_{21}} \right) -$$

$$2 \text{Sin}[\theta] \text{Cos}[\theta] \left(-i \alpha \frac{n_2 h_{11} e^{n_2 x_{1+1} \text{Sin}[\theta]} - n_1 h_{12} e^{n_1 x_{1+1} \text{Sin}[\theta]}}{h_{11} h_{22} - h_{12} h_{21}} \right)$$

$$x_{211t} = -\text{Sin}[\theta] \text{Cos}[\theta] \left(\frac{n_1^2 h_{22} e^{n_1 x_{1+1} \text{Sin}[\theta]} - n_2^2 h_{21} e^{n_2 x_{1+1} \text{Sin}[\theta]}}{h_{11} h_{22} - h_{12} h_{21}} \right) +$$

$$\text{Sin}[\theta] \text{Cos}[\theta] \left(-\alpha^2 \frac{h_{22} e^{n_1 x_{1+1} \text{Sin}[\theta]} - h_{21} e^{n_2 x_{1+1} \text{Sin}[\theta]}}{h_{11} h_{22} - h_{12} h_{21}} \right) +$$

$$(\text{Cos}[\theta]^2 - \text{Sin}[\theta]^2) \left(-i \alpha \frac{n_1 h_{22} e^{n_1 x_{1+1} \text{Sin}[\theta]} - n_2 h_{21} e^{n_2 x_{1+1} \text{Sin}[\theta]}}{h_{11} h_{22} - h_{12} h_{21}} \right)$$

$$\begin{aligned}
x_{221t} = & -\text{Sin}[\theta] \text{Cos}[\theta] \left(\frac{n_2^2 h_{11} e^{n_2 x_{i+1} \text{Sin}[\theta]} - n_1^2 h_{12} e^{n_1 x_{i+1} \text{Sin}[\theta]}}{h_{11} h_{22} - h_{12} h_{21}} \right) + \\
& \text{Sin}[\theta] \text{Cos}[\theta] \left(-\alpha^2 \frac{h_{11} e^{n_2 x_{i+1} \text{Sin}[\theta]} - h_{12} e^{n_1 x_{i+1} \text{Sin}[\theta]}}{h_{11} h_{22} - h_{12} h_{21}} \right) + \\
& (\text{Cos}[\theta]^2 - \text{Sin}[\theta]^2) \left(-i \alpha \frac{n_2 h_{11} e^{n_2 x_{i+1} \text{Sin}[\theta]} - n_1 h_{12} e^{n_1 x_{i+1} \text{Sin}[\theta]}}{h_{11} h_{22} - h_{12} h_{21}} \right)
\end{aligned}$$

$x_{112tc} = \text{Conjugate}[x_{112t}]$, $x_{122tc} = \text{Conjugate}[x_{122t}]$, $x_{212tc} = \text{Conjugate}[x_{212t}]$,
 $x_{222tc} = \text{Conjugate}[x_{222t}]$, $x_{111tc} = \text{Conjugate}[x_{111t}]$, $x_{121tc} = \text{Conjugate}[x_{121t}]$,
 $x_{211tc} = \text{Conjugate}[x_{211t}]$ and $x_{221tc} = \text{Conjugate}[x_{221t}]$.

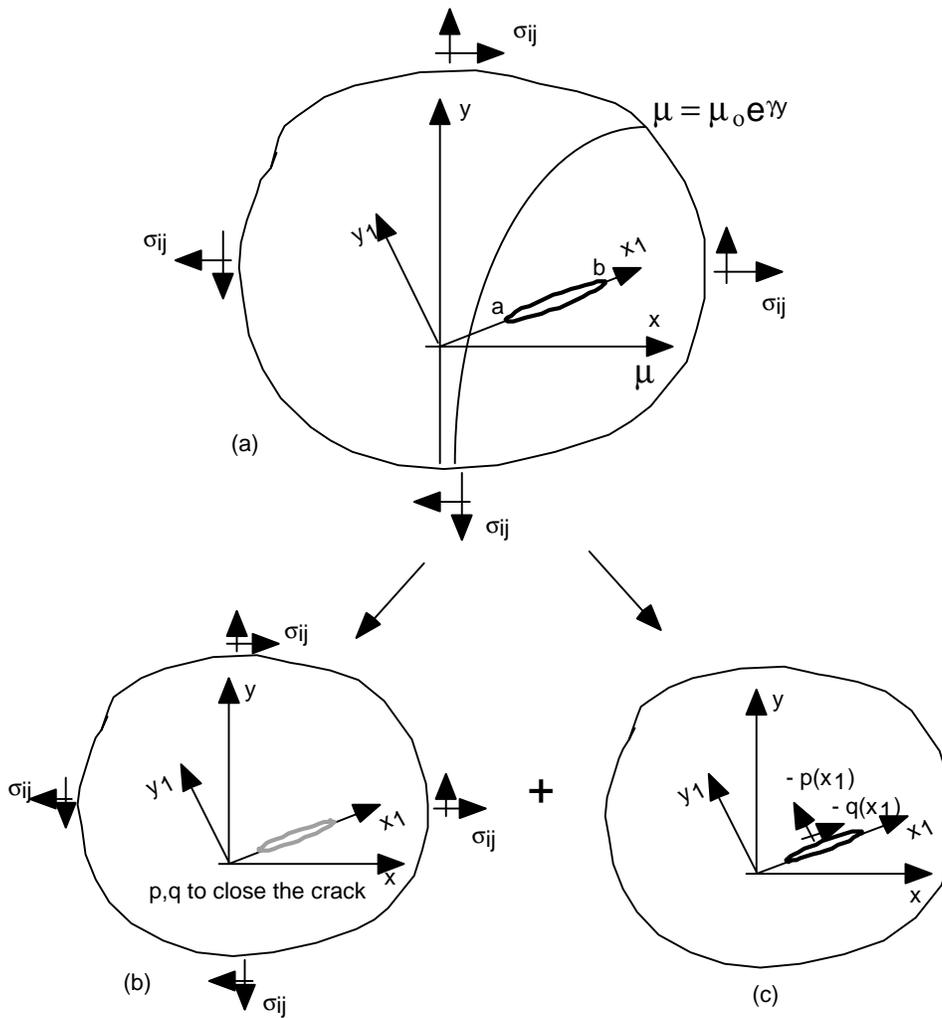


Figure 1. Methodology of Solution for the Fundamental Problem.

(a) Mixed Boundary Value Problem for the FGM.

(b) Infinite FGM Plate without Crack.

(c) Perturbation Problem of a Crack loaded by Surface Traction.

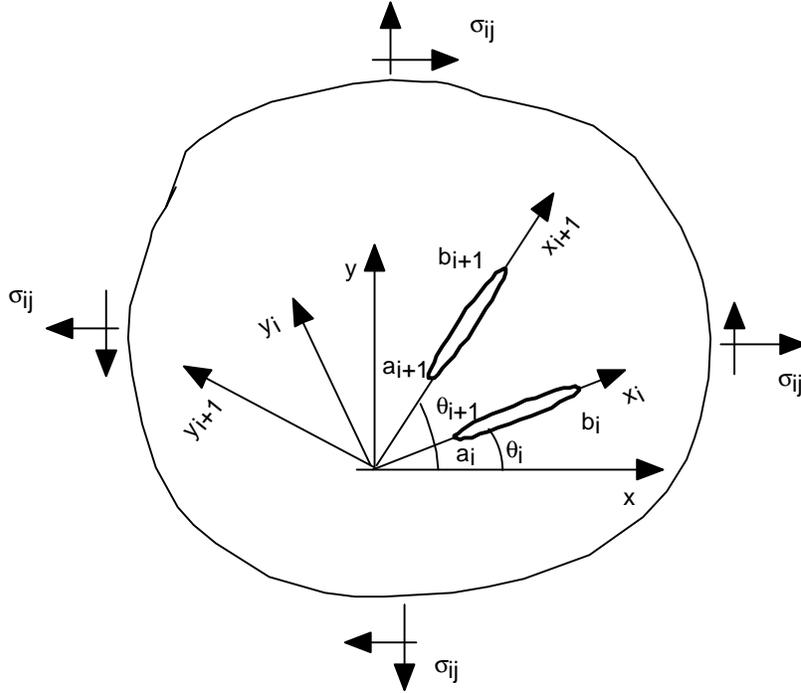


Figure 2. Multiple Cracks Embedded in the Infinite FGM Plate.

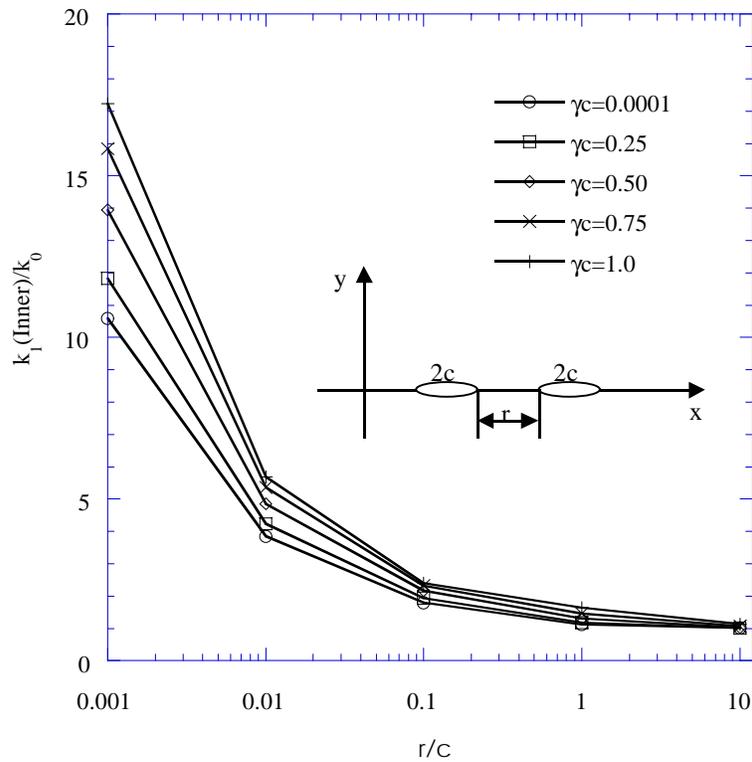


Figure 3. Mode I normalized SIF versus normalized inner crack tips distance for two collinear horizontal cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$).

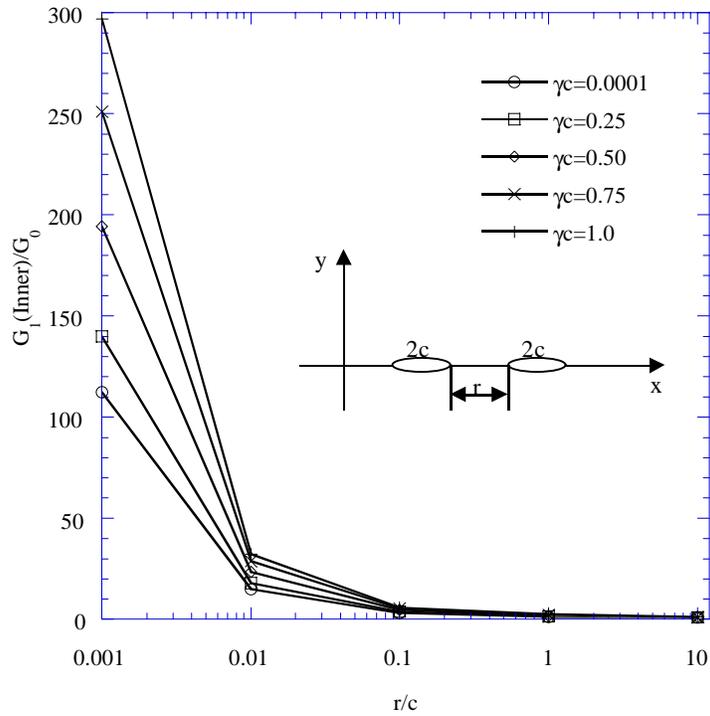


Figure 4. Mode I normalized SERR versus normalized inner crack tips distance for two collinear horizontal cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$).

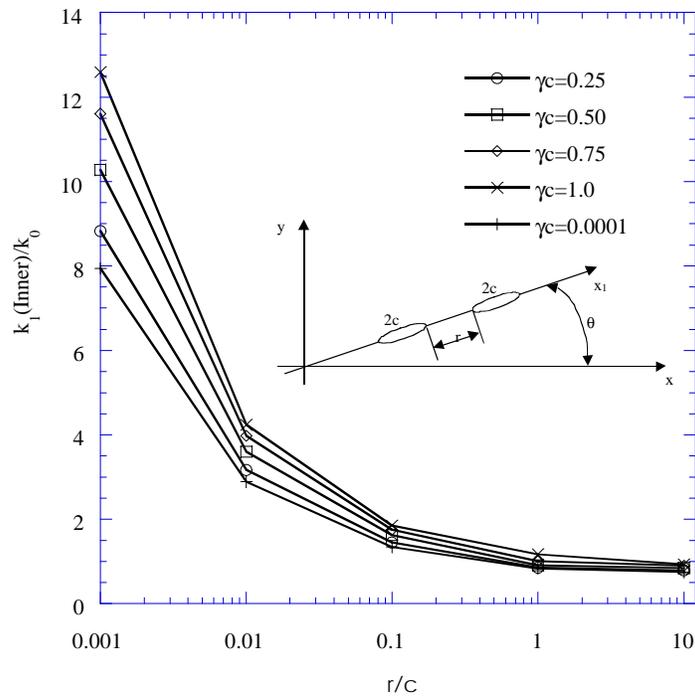


Figure 5. Mode I normalized SIF versus normalized inner crack tips distance for two collinear cracks along the $\theta=30$ deg. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$).

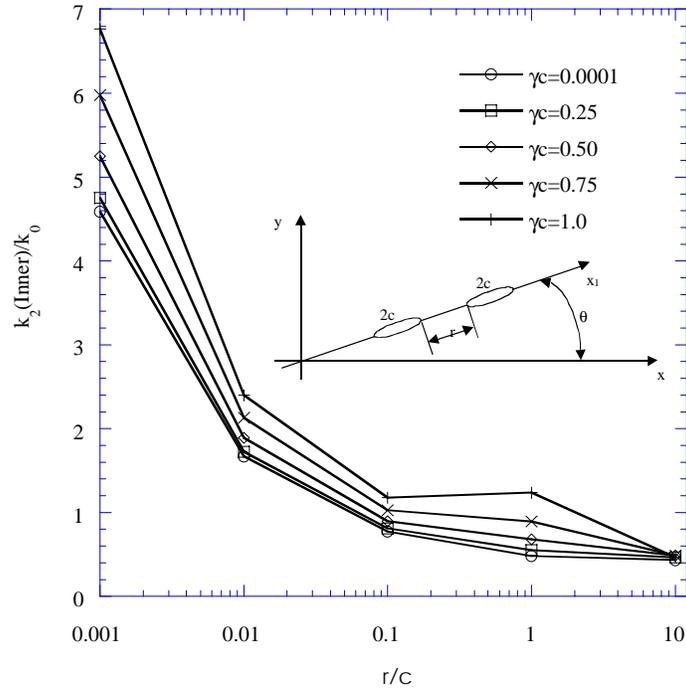


Figure 6. Mode II normalized SIF versus normalized inner crack tips distance for two collinear cracks along the $\theta=30$ deg. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$).

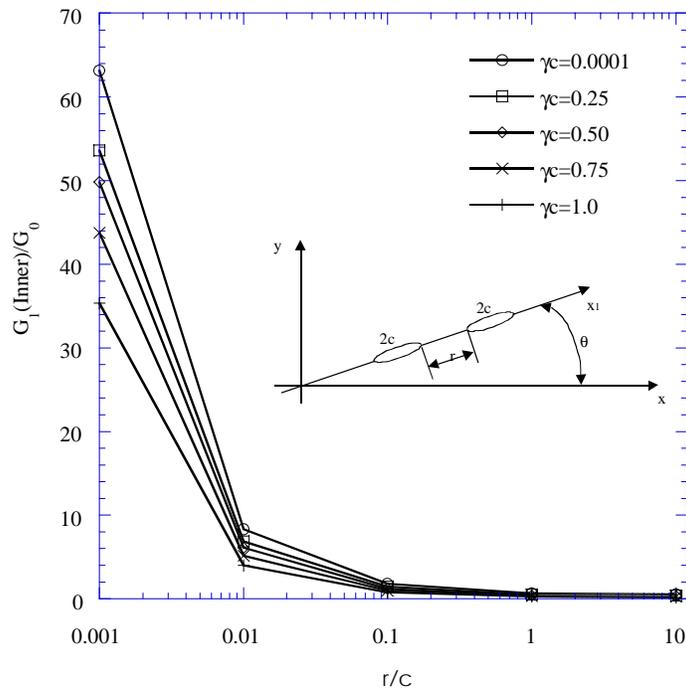


Figure 7. Mode I normalized SERR versus normalized inner crack tips distance for two collinear cracks along the $\theta=30$ deg. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$).

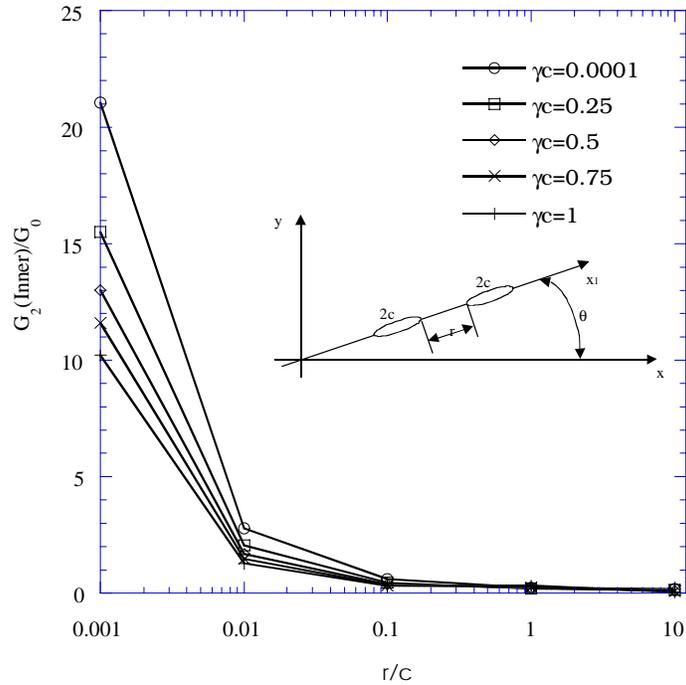


Figure 8. Mode II normalized SERR versus normalized inner crack tips distance for two collinear cracks along the $\theta=30$ deg. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$).

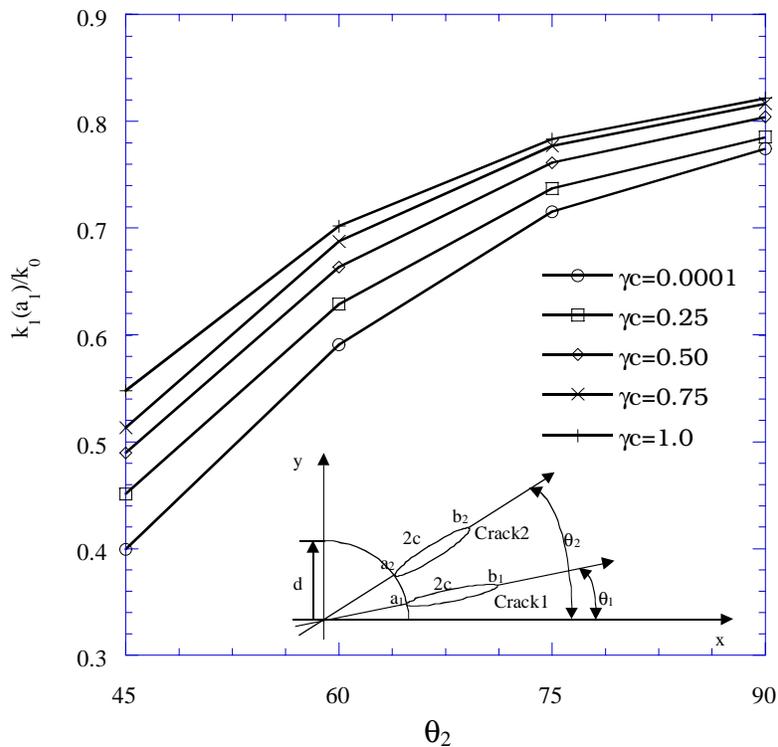


Figure 9. Mode I normalized SIF at the tip a_1 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

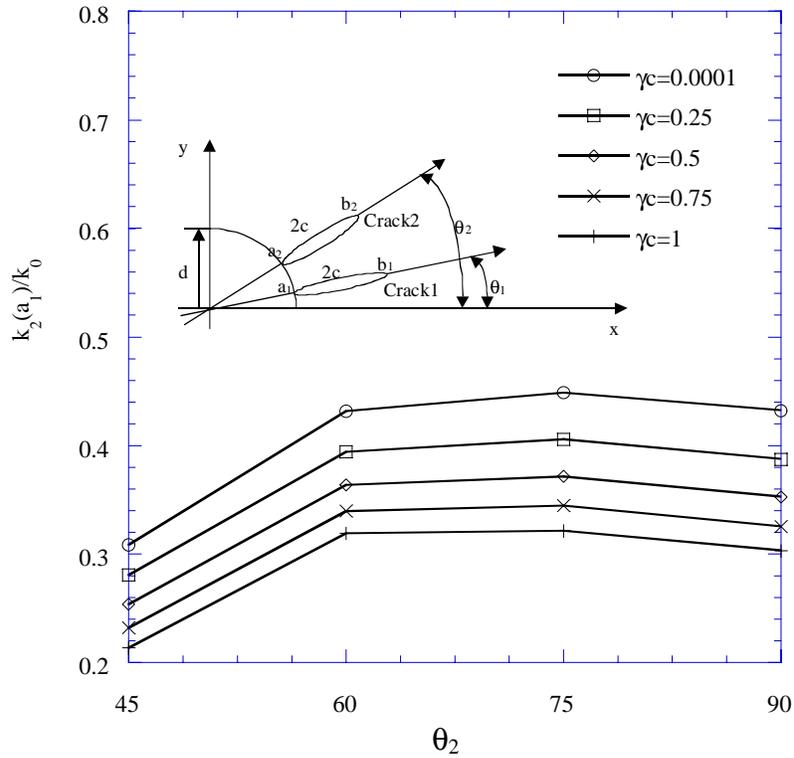


Figure 10. Mode II normalized SIF at the tip a_1 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

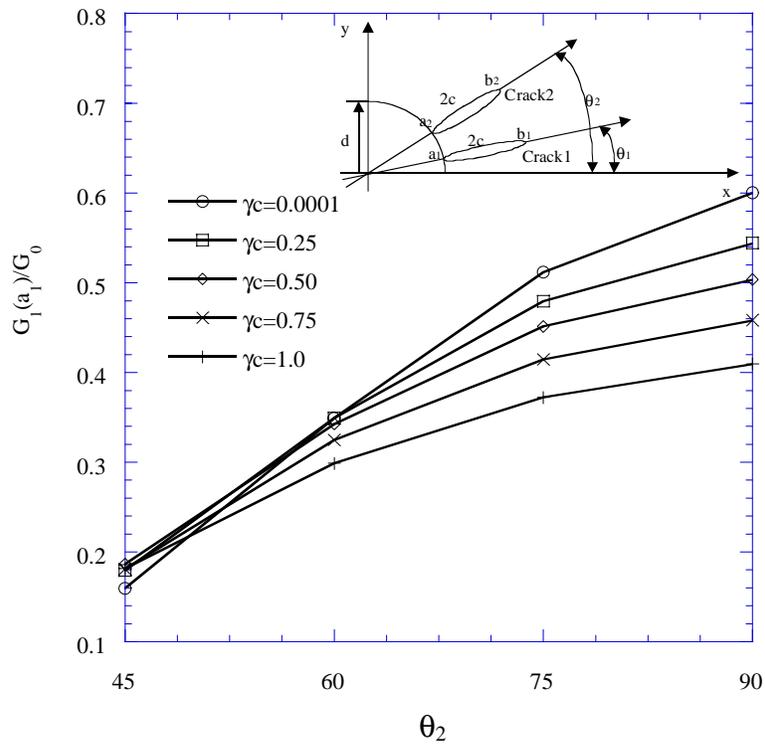


Figure 11. Mode I normalized SERR at the tip a_1 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

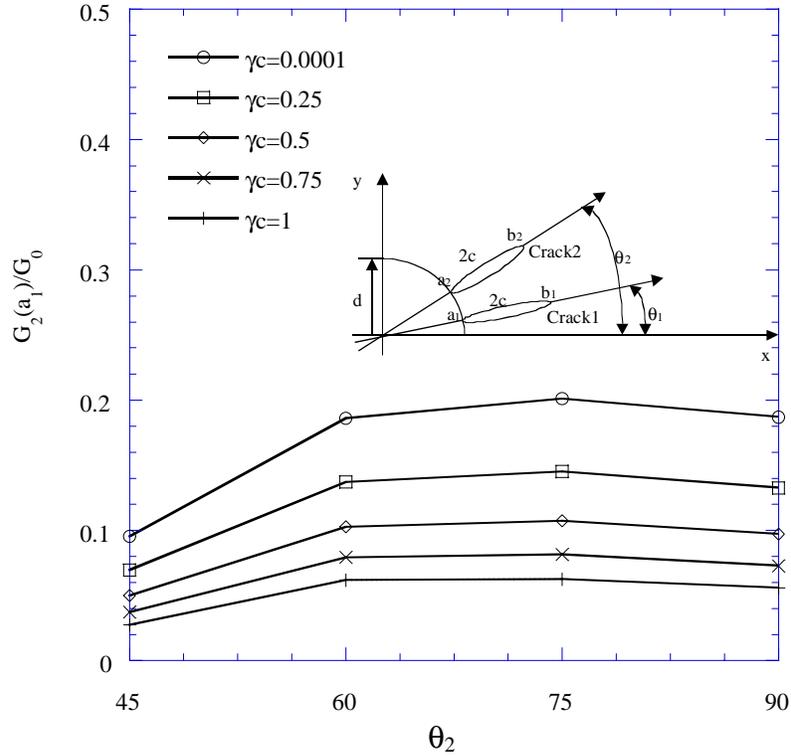


Figure 12. Mode II normalized SERR at the tip a_1 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

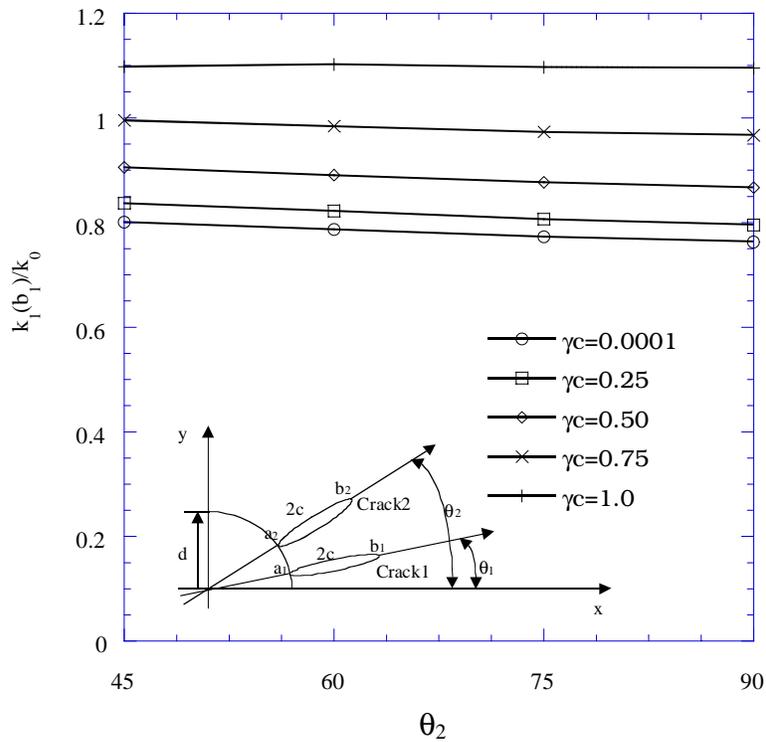


Figure 13. Mode I normalized SIF at the tip b_1 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

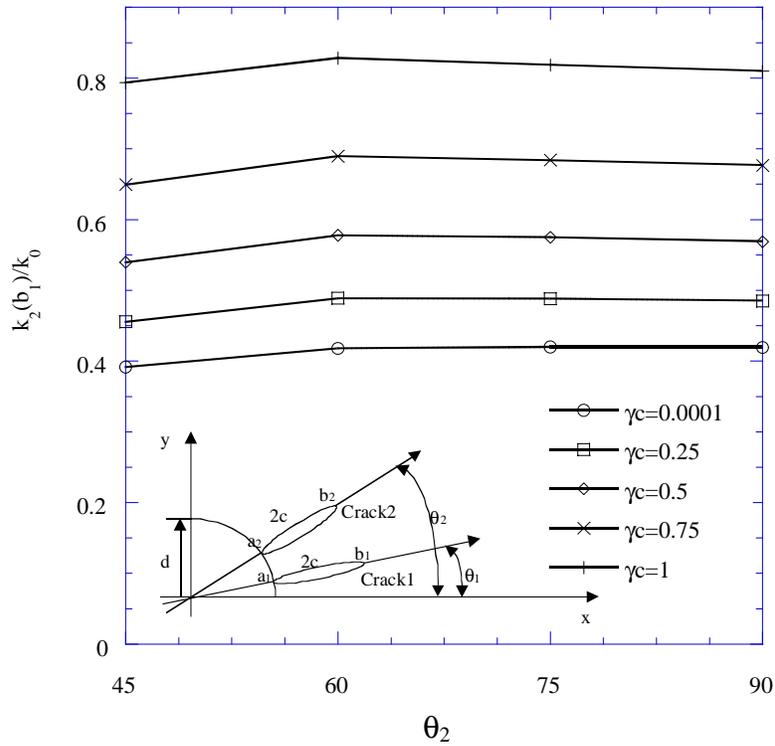


Figure 14. Mode II normalized SIF at the tip b_1 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

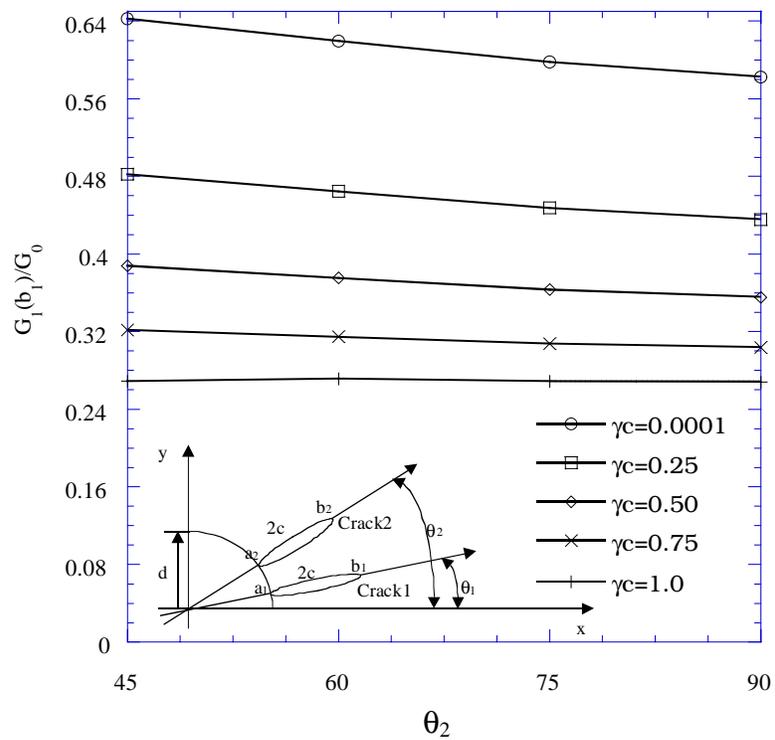


Figure 15. Mode I normalized SERR at the tip b_1 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

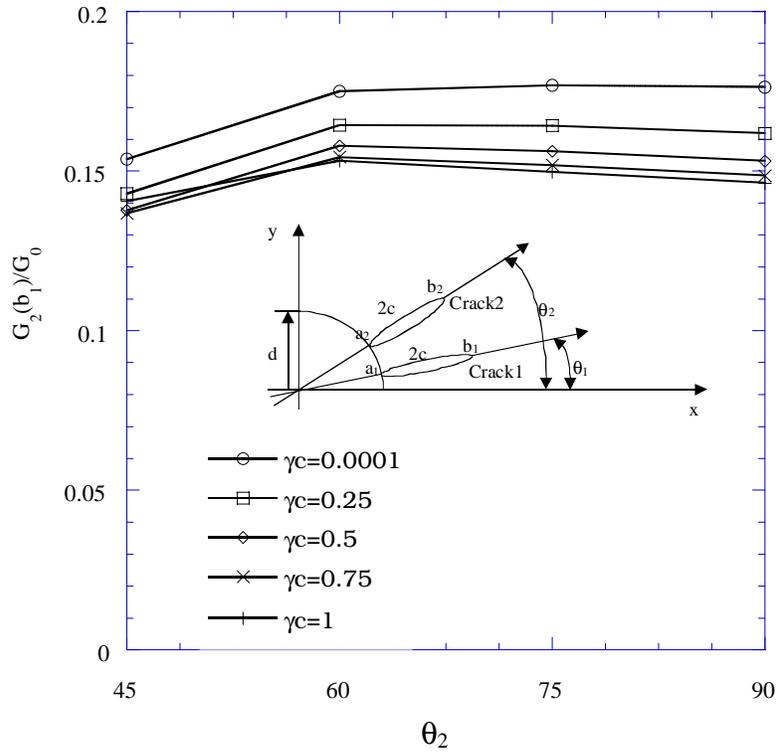


Figure 16. Mode II normalized SERR at the tip b_1 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

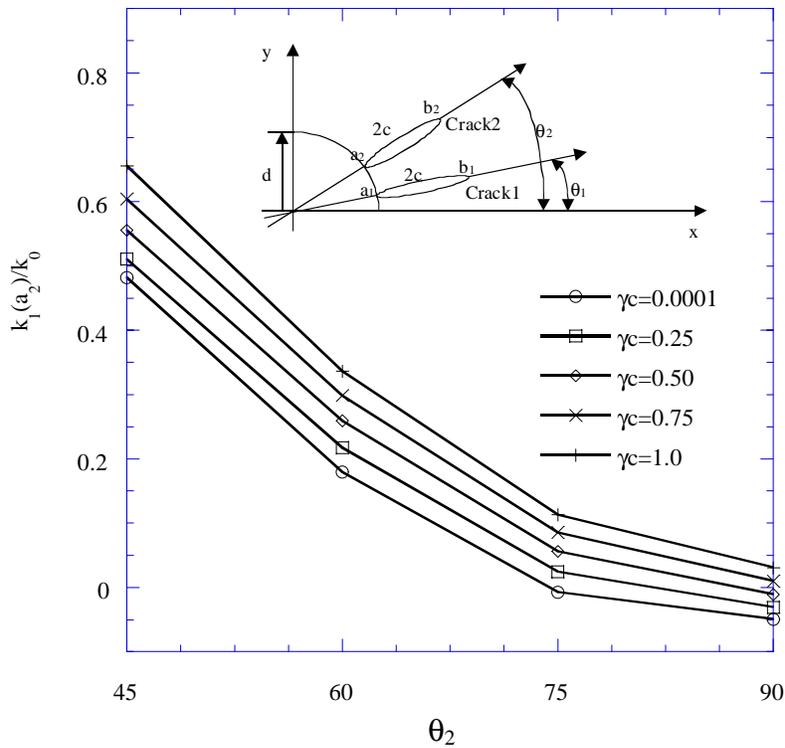


Figure 17. Mode I normalized SIF at the tip a_2 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

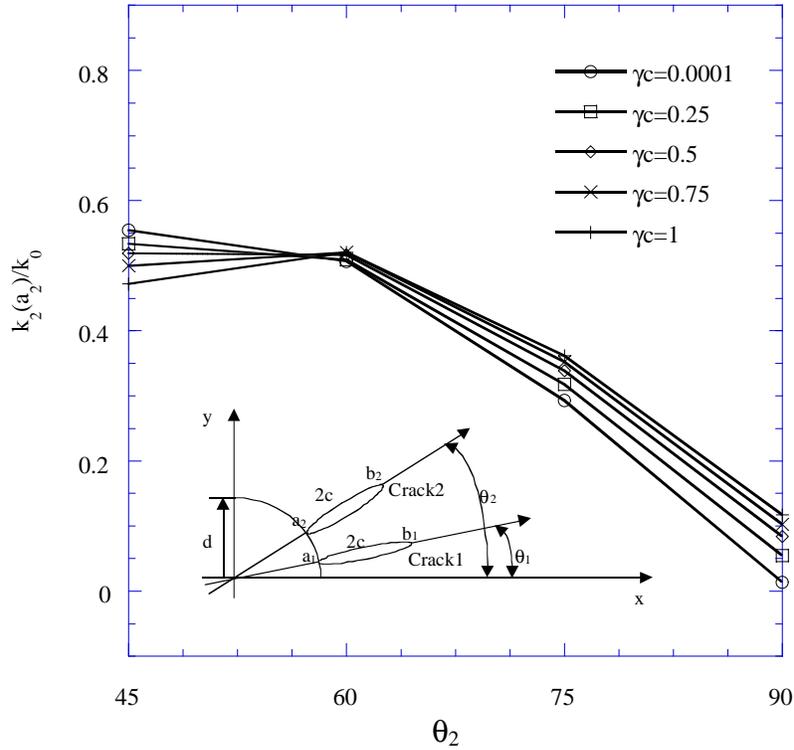


Figure 18. Mode II normalized SIF at the tip a_2 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

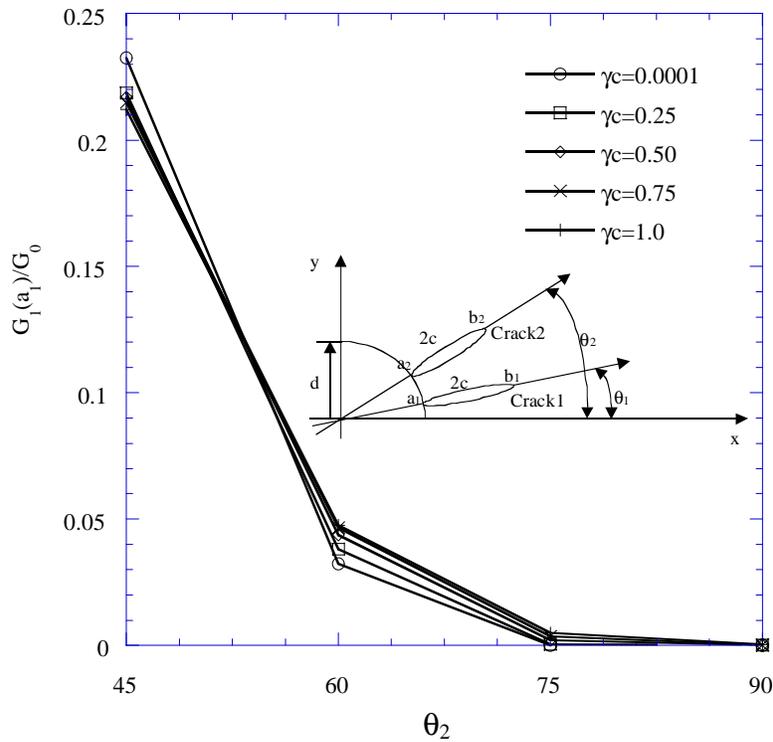


Figure 19. Mode I normalized SERR at the tip a_2 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

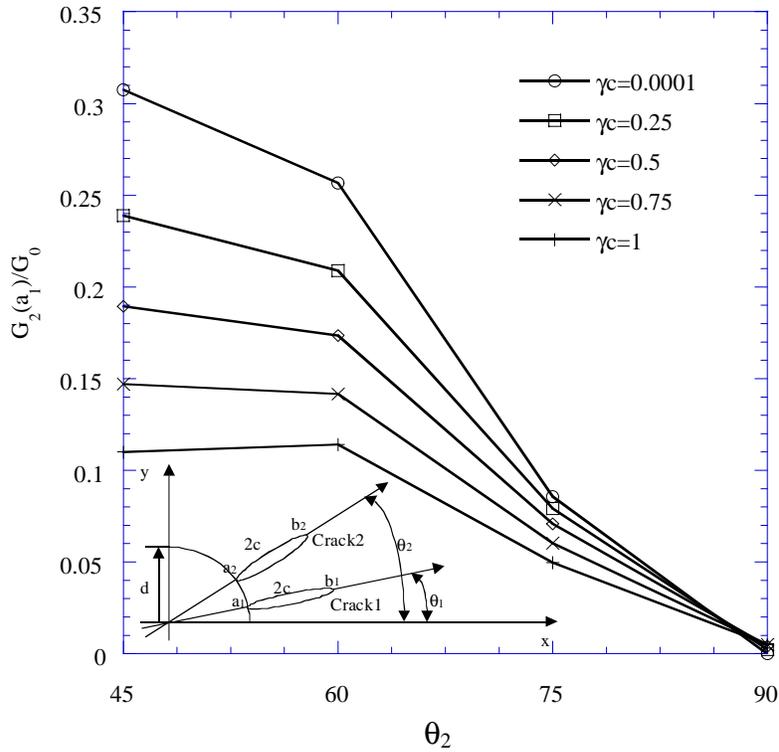


Figure 20. Mode II normalized SERR at the tip a_2 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

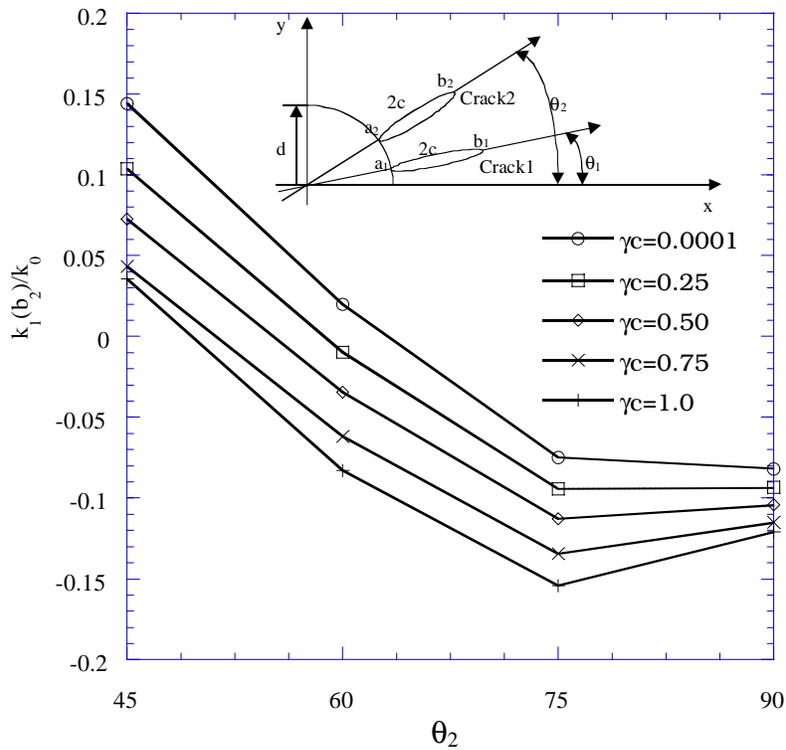


Figure 21. Mode I normalized SIF at the tip b_2 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

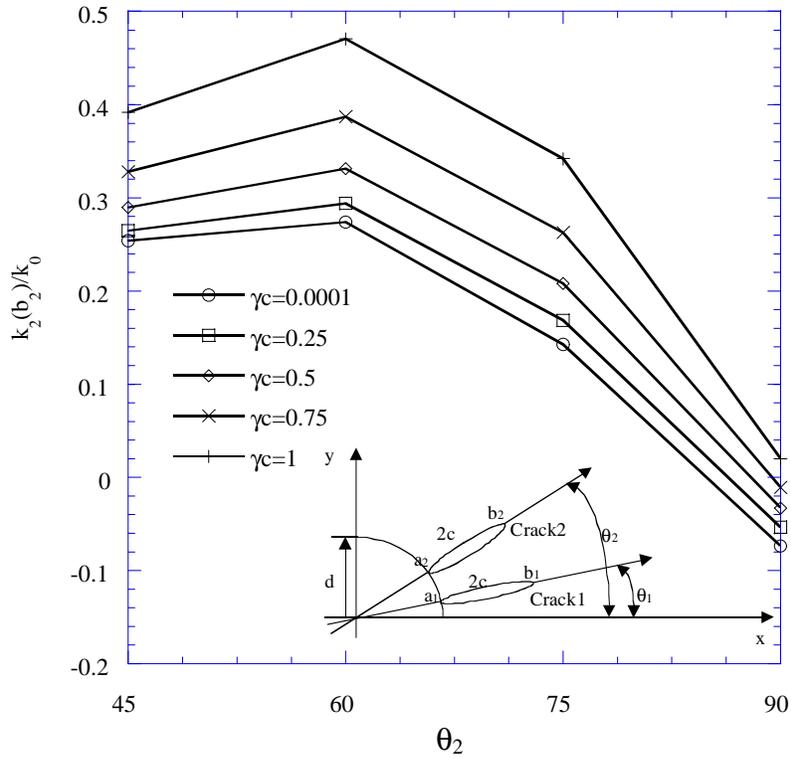


Figure 22. Mode II normalized SIF at the tip b_2 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0, \sigma_{xx} = \sigma_{xy} = 0.0, d = 1.0, \theta_1 = 30$ deg.).

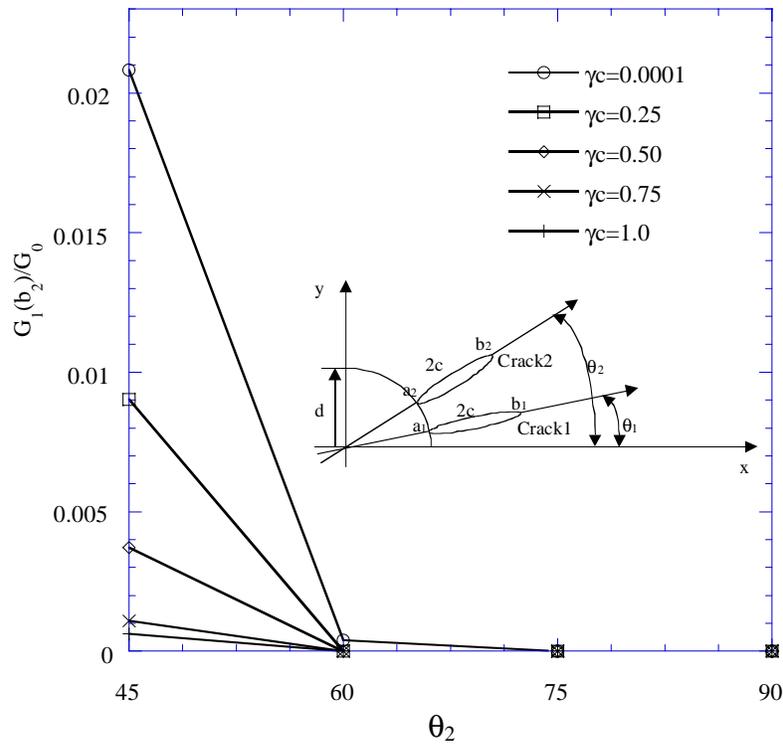


Figure 23. Mode I normalized SERR at the tip b_2 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0, \sigma_{xx} = \sigma_{xy} = 0.0, d = 1.0, \theta_1 = 30$ deg.).

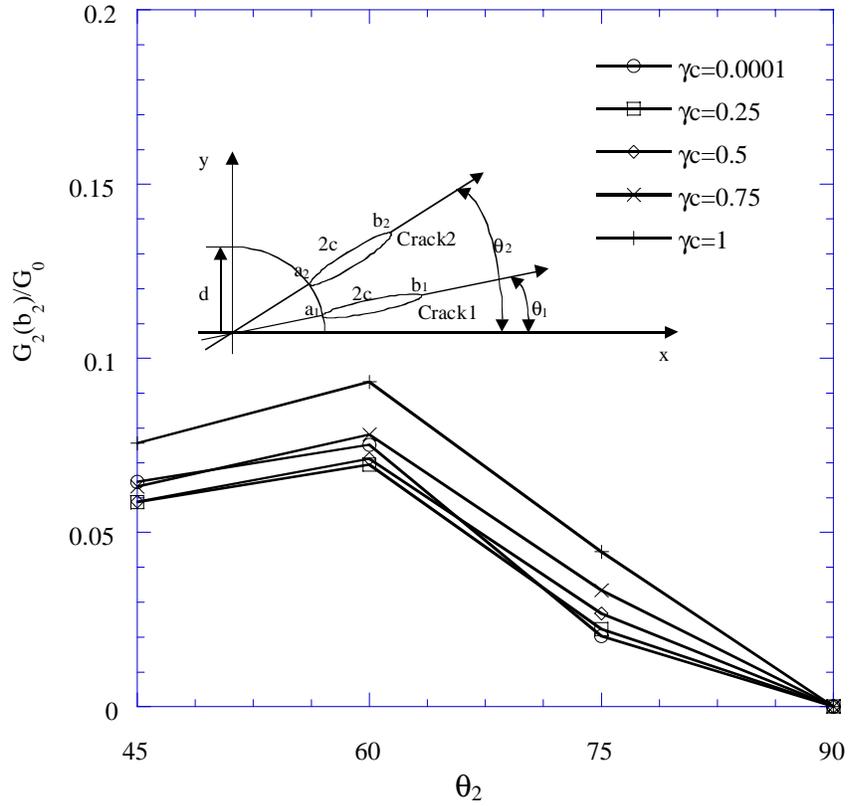


Figure 24. Mode II normalized SERR at the tip b_2 versus crack (2) orientation angle θ_2 for two inclined cracks. ($\sigma_{yy} = 1.0$, $\sigma_{xx} = \sigma_{xy} = 0.0$, $d=1.0$, $\theta_1=30$ deg.).

REPORT DOCUMENTATION PAGE			<i>Form Approved</i> <i>OMB No. 0704-0188</i>	
Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.				
1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE February 1999	3. REPORT TYPE AND DATES COVERED Final Contractor Report	
4. TITLE AND SUBTITLE Analysis of Multiple Cracks in an Infinite Functionally Graded Plate			5. FUNDING NUMBERS WU-537-04-22-00 NAG3-2201	
6. AUTHOR(S) N.I. Shbeeb, W.K. Binienda, and K.L. Kreider				
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) The University of Akron Department of Civil Engineering Akron, Ohio 44325-3905			8. PERFORMING ORGANIZATION REPORT NUMBER E-11406	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Lewis Research Center Cleveland, Ohio 44135-3191			10. SPONSORING/MONITORING AGENCY REPORT NUMBER NASA CR-1999-208676	
11. SUPPLEMENTARY NOTES Project Manager, Gary R. Halford, Research and Technology Directorate, NASA Lewis Research Center, organization code 5000, (216) 433-3265.				
12a. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified - Unlimited Subject Category: 39 This publication is available from the NASA Center for AeroSpace Information, (301) 621-0390.			12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) A general methodology was constructed to develop the fundamental solution for a crack embedded in an infinite non-homogeneous material in which the shear modulus varies exponentially with the y coordinate. The fundamental solution was used to generate a solution to fully interactive multiple crack problems for stress intensity factors and strain energy release rates. Parametric studies were conducted for two crack configurations. The model displayed sensitivity to crack distance, relative angular orientation, and to the coefficient of nonhomogeneity.				
14. SUBJECT TERMS Functionally graded materials; Thermomechanical load cycles; Isotropic; Poisson's ratio; Young's modulus; Strain-energy; Airy stress; Boundary value problems			15. NUMBER OF PAGES 54	
			16. PRICE CODE A04	
17. SECURITY CLASSIFICATION OF REPORT Unclassified	18. SECURITY CLASSIFICATION OF THIS PAGE Unclassified	19. SECURITY CLASSIFICATION OF ABSTRACT Unclassified	20. LIMITATION OF ABSTRACT	