

NASA/TM—2000-210033



# Processing and Properties of SiC/MoSi<sub>2</sub>-SiC Composites Fabricated by Melt Infiltration

Ramakrishna T. Bhatt

U.S. Army Research Laboratory, Glenn Research Center, Cleveland, Ohio

Mohan G. Hebsur

Ohio Aerospace Institute, Brook Park, Ohio

## The NASA STI Program Office . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) Program Office plays a key part in helping NASA maintain this important role.

The NASA STI Program Office is operated by Langley Research Center, the Lead Center for NASA's scientific and technical information. The NASA STI Program Office provides access to the NASA STI Database, the largest collection of aeronautical and space science STI in the world. The Program Office is also NASA's institutional mechanism for disseminating the results of its research and development activities. These results are published by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA's counterpart of peer-reviewed formal professional papers but has less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.

- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or cosponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services that complement the STI Program Office's diverse offerings include creating custom thesauri, building customized data bases, organizing and publishing research results . . . even providing videos.

For more information about the NASA STI Program Office, see the following:

- Access the NASA STI Program Home Page at <http://www.sti.nasa.gov>
- E-mail your question via the Internet to [help@sti.nasa.gov](mailto:help@sti.nasa.gov)
- Fax your question to the NASA Access Help Desk at (301) 621-0134
- Telephone the NASA Access Help Desk at (301) 621-0390
- Write to:  
NASA Access Help Desk  
NASA Center for Aerospace Information  
7121 Standard Drive  
Hanover, MD 21076

NASA/TM—2000-210033



# Processing and Properties of SiC/MoSi<sub>2</sub>-SiC Composites Fabricated by Melt Infiltration

Ramakrishna T. Bhatt

U.S. Army Research Laboratory, Glenn Research Center, Cleveland, Ohio

Mohan G. Hebsur

Ohio Aerospace Institute, Brook Park, Ohio

Prepared for the  
24th Annual Conference on Composites, Advanced Ceramics Materials, and Structures  
sponsored by the American Ceramic Society  
Cocoa Beach, Florida, January 23–28, 2000

National Aeronautics and  
Space Administration

Glenn Research Center

---

May 2000

Trade names or manufacturers' names are used in this report for identification only. This usage does not constitute an official endorsement, either expressed or implied, by the National Aeronautics and Space Administration.

Available from

NASA Center for Aerospace Information  
7121 Standard Drive  
Hanover, MD 21076  
Price Code: A03

National Technical Information Service  
5285 Port Royal Road  
Springfield, VA 22100  
Price Code: A03

# **PROCESSING AND PROPERTIES OF SiC/MoSi<sub>2</sub>-SiC COMPOSITES FABRICATED BY MELT INFILTRATION**

Ramakrishna T. Bhatt  
U.S. Army Research Laboratory  
National Aeronautics and Space Administration  
Glenn Research Center  
Cleveland, Ohio 44135

Mohan G. Hebsur  
Ohio Aerospace Institute  
Brook Park, Ohio 44142

## **ABSTRACT**

Hi-Nicalon SiC fiber reinforced MoSi<sub>2</sub>-SiC matrix composites (SiC/MoSi<sub>2</sub>-SiC) have been fabricated by the melt infiltration approach. The composite consists of ~60 vol%, 2-D woven BN/SiC coated Hi-Nicalon SiC fibers and ~40 vol% MoSi<sub>2</sub>-SiC matrix. The room temperature tensile properties and thermal conductivity of the SiC/MoSi<sub>2</sub>-SiC composites were measured and compared with those of the melt infiltrated SiC/SiC composites. The influence of fiber architecture on tensile properties was also evaluated. Results indicate that the primary modulus, stress corresponding to deviation from linearity, and transverse thermal conductivity values for the SiC/MoSi<sub>2</sub>-SiC composites are significantly lower than those for the SiC/SiC composites. Microcracking of the matrix due to the large difference in thermal expansion between MoSi<sub>2</sub> and SiC appears to be the reason for the lower matrix dominated properties of SiC/MoSi<sub>2</sub>-SiC composites.

## **INTRODUCTION**

Advanced high temperature materials are needed for successfully developing future generations of aerospace propulsion and power systems. Because of its high melting point, elevated temperature oxidation resistance, brittle to ductile transition, and high electrical and thermal conductivity, molybdenum silicide (MoSi<sub>2</sub>) is considered to be a promising high temperature structural material for next generation turbine components [1]. However, the use of MoSi<sub>2</sub> has been hindered due to the brittle nature of the material at low temperatures, inadequate

creep resistance at high temperatures and poor oxidation resistance from 450 to 550 °C [1]. In recent years significant progress has been made in improving the properties of MoSi<sub>2</sub>. For example, creep resistance has been improved by alloying MoSi<sub>2</sub> with W or Re [2,3]; the low temperature toughness problem has been improved by particulate or fiber reinforcements [4-6]; and the intermediate temperature pest oxidation problem has been mitigated by dispersions of Si<sub>3</sub>N<sub>4</sub> or Ge [7,8].

Currently, unreinforced and reinforced MoSi<sub>2</sub> materials are fabricated by hot pressing or hot isostatically pressing. With these methods only simple shapes can be fabricated. Even though MoSi<sub>2</sub> is electrically conductive and can be electro-discharge machined, fabrication of complex shape components from a hot pressed block is very expensive and time consuming. Therefore, cost effective, near net shape processing approaches are needed for utilization of MoSi<sub>2</sub> components in turbines. Among many fabrication approaches, the non-reactive melt infiltration approach appears to be best suited for MoSi<sub>2</sub>. This approach has been successfully adopted for fabrication of SiC/SiC composites. One draw back of this process is that it leaves excess silicon metal, which may limit the upper temperature capability of the material. However, excess silicon can be converted to MoSi<sub>2</sub> by displacement or combination reaction by selecting Mo<sub>2</sub>C or Mo<sub>5</sub>Si<sub>3</sub> as a starting material [9].

This study had three objectives: First, to fabricate SiC/MoSi<sub>2</sub>-SiC composites by the MI approach; second, to measure their properties and compare them with those of the SiC/SiC composites fabricated by a similar approach; third, to determine potential performance advantages of 2-D woven SiC/MoSi<sub>2</sub>-SiC composites for high temperature applications.

## EXPERIMENTAL

The starting materials for composite fabrication were BN/SiC coated Hi-Nicalon<sup>TM</sup> SiC fiber preforms, MoSi<sub>2</sub> and SiC powders. The preforms of BN/SiC coated Hi-Nicalon<sup>TM</sup> SiC fibers were purchased from Honeywell Advanced Composites Inc. The Nippon Carbon Company, Japan fabricated the Hi-Nicalon fibers and Albany International Techniweave, Inc. Rochester, prepared the woven fiber mats. Three different 2-D fiber architectures were examined: PW (plain weave), 5HS (5 harness satin), and 8HS. The MoSi<sub>2</sub> and SiC powders with average particle diameters of ~75 and ~3 μm, respectively, were purchased from H.C. Stark. For composite fabrication, the preforms were fabricated by stacking 8 layers 2-D woven SiC fiber mat in a graphite fixture and depositing an ~0.5 μm thick BN layer and a 3-5 μm thick SiC layer (both by chemical vapor infiltration (CVI)). The nominal dimensions of the preforms after CVI coating were 229-mm (L) x 152-mm (W) x 2-mm (T). The preforms contained

~ 40 vol. % SiC fibers, ~18-30 vol% BN/SiC interface coating, and 20-40% interconnected open porosity.

The preforms were cut into smaller specimens of dimensions with 152 mm (L) x 12.5 mm (W) x 2 mm (T)) using a diamond impregnated metal bonded cutoff wheel and water based grinding fluid. The cut specimens were soaked in a degreasing solution for 24 hrs, and then dried in an oven maintained at 100 °C.

The MoSi<sub>2</sub> and SiC powders were dry attrition milled in a stainless steel vessel using 6-mm WC balls as grinding medium. The outer surface of the vessel was cooled with liquid nitrogen. A typical batch contained a 50:50 mixture of MoSi<sub>2</sub> and SiC powders. A grinding medium to powder ratio of 20:1 was used. Attrition milling was performed for 16 hrs in flowing argon gas. The milled powder was stored in a glove box filled with nitrogen. The average particle diameter after attrition milling was ~ 5 μm.

For slurry preparation, the attrition milled MoSi<sub>2</sub> and SiC powder mixtures were blended with a commercially available binder, dispersant, and wetting agent. NH<sub>4</sub>OH was added to the slurry to adjust p<sub>H</sub> to ~9.

### **Composite fabrication**

Slurry infiltration into the preform specimen was conducted in a stainless steel (SS) chamber equipped with three ports. One port was connected to a forepump for evacuating the chamber; one port was used for poring slurry into the chamber; and one was connected to a compressed air source for pressurizing the chamber. A plaster of Paris mold with a cavity was fabricated. The mold, with the specimen, was placed inside the SS chamber. The chamber was evacuated to 10<sup>-4</sup> Torr and then the port connected to the vacuum pump was closed off. Through the second port, the slurry was poured over the preform placed on the plaster of Paris mold and the port was closed off. Through the third port, compressed air was bled into the SS chamber until chamber pressure reached 3 MPa. The air pressure was maintained for several hours until the slurry infiltrated into the preform, and the water present in the slurry had completely seeped into the plaster of Paris mold. Subsequently, any excess powder present on the surface of the preform specimen was dusted off. The MoSi<sub>2</sub>-SiC particle-filled specimen was transferred to a vacuum furnace lined with graphite heating elements and fixtures. An appropriate amount of electronic grade silicon was placed over the specimen. The furnace was evacuated to 10<sup>-4</sup> Torr, heated to 1420 °C for 30 minutes allowing the silicon melt to infiltrate the particle filled specimen, and then cooled slowly to room temperature.

## **Specimen preparation**

Some of the specimens were sectioned, mounted in a metallographic mold, ground successively on 40  $\mu\text{m}$  down to 1- $\mu\text{m}$  diamond particle impregnated metal disks, and polished in a vibratory polisher on a micro-cloth using 0.3  $\mu\text{m}$  diamond powder paste. The mounted specimens were coated with a thin layer of carbon or palladium in a vacuum evaporator to avoid charging during observation in a scanning electron microscope (SEM).

For tensile testing, dog-bone shaped specimens were machined from the composite plate using an ultrasonic, SiC-slurry impact machine. At each specimen end, two glass fiber-reinforced epoxy tabs of dimension 37 mm x 12 mm x 1 mm were bonded, leaving ~60 mm for the gage section. A spring-loaded clip-on gage was attached to the gage section of the specimen to monitor the strain during the tensile test. The specimens were tested at room temperature until failure in a servo-controlled tensile testing machine equipped with self-aligning grips at a crosshead speed of 1.3 mm/min.

For comparison purposes, a panel of Hi-Nicalon SiC/SiC composite fabricated by the MI process was purchased from Honeywell Advanced Composites Inc. This composite was tested using the same approach that was used with the Hi-Nicalon SiC/MoSi<sub>2</sub>-SiC composites.

For thermal diffusivity measurement, ~9-mm x 9-mm specimens were cut from a larger composite specimen. Thermophysics Laboratory, Blacksburg, VA, measured the transverse thermal diffusivity of the Hi-Nicalon SiC/MoSi<sub>2</sub>-SiC and SiC/SiC composite specimens in argon at temperatures from 25 to 1400 °C.

## **RESULTS**

### **Microstructure**

SEM photographs of the cross-section of the Hi-Nicalon SiC/MoSi<sub>2</sub>-SiC composites are shown in Fig. 1. This figure indicates the matrix is well infiltrated in the pore spaces of the SiC preform. The light regions in figure 1(a) are the MoSi<sub>2</sub>-SiC matrix and the darker regions are the BN/SiC coated Hi-Nicalon woven mats. Figures 1(b) and 1(c) are higher magnification photographs of the matrix and interface regions. The brighter particles in Fig. 1(b) are MoSi<sub>2</sub> and the dark particles are SiC. The phase surrounding the MoSi<sub>2</sub> and SiC particles is silicon. Figure 1(c) shows no evidence of reaction between the CVI SiC coating and the matrix.

### **Tensile properties**

The room-temperature tensile stress-strain behavior for the 5HS Hi-Nicalon SiC/SiC and SiC/MoSi<sub>2</sub>-SiC composites is shown in figure 2. Also included in the

figure for comparison is the stress-strain behavior of 5HS Hi-Nicalon SiC/Epoxy composite. The stress-strain behaviors generally show two regions: an initial elastic region and a non-linear region. Comparison of the stress-strain behaviors indicates major differences in the stress corresponding to deviation

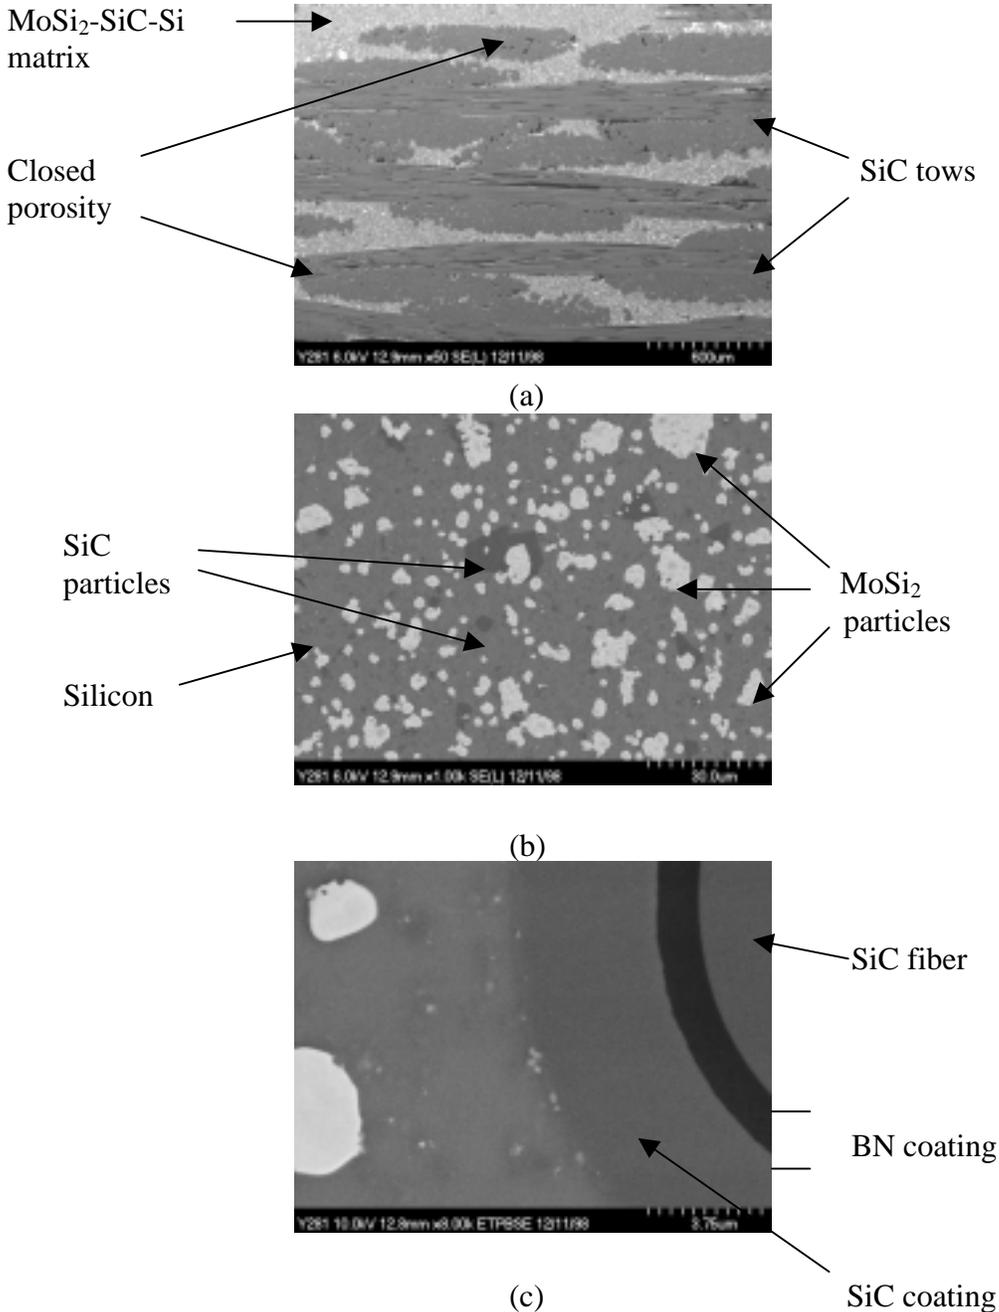


Fig.1 SEM micrographs of the cross section of a 5HS Hi-Nicalon SiC/MoSi<sub>2</sub>-SiC composite showing various microstructural features: (a) distribution of the matrix within the preform, (b) distribution of particles in the matrix, and (c) the CVI SiC coating/matrix interface region.

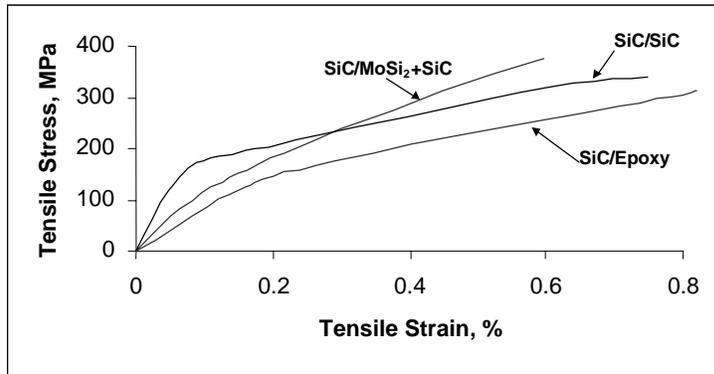


Fig. 2 Room temperature tensile stress-strain behavior for the 5HS Hi-Nicalon SiC/MoSi<sub>2</sub>-SiC, SiC/SiC, and SiC/epoxy composites

from linearity (DFL) and the primary elastic modulus, but the ultimate tensile strengths for all three composites are nearly the same suggesting minimal degradation of SiC fibers, or the BN/SiC interface coatings during processing. The room-temperature tensile property data for the PW, 5HS, and 8HS Hi-Nicalon SiC/MoSi<sub>2</sub>-SiC, 5HS SiC/SiC and 5HS SiC/epoxy composites are summarized in Table I. Data represent an average of 3 specimens for each composite type. Noticeable features in Table I are that the fiber architecture shows no major effect on the tensile properties of SiC/MoSi<sub>2</sub>-SiC composites. Also, the primary modulus and DFL stress for SiC/MoSi<sub>2</sub>-SiC composites are moderately higher than that for the Nicalon SiC/epoxy composites, but lower than that for the SiC/SiC composites. Theoretically, the initial elastic modulus of SiC/MoSi<sub>2</sub>-SiC composites and SiC/SiC composites should be the same because MoSi<sub>2</sub> and SiC materials have similar elastic moduli. It is suspected that the lower primary elastic

Table I Room temperature tensile data for Hi-Nicalon SiC/Epoxy, SiC/MoSi<sub>2</sub>-SiC, and SiC/SiC composites.

Composites	Lay up	DFL, MPa	DFL, %	E, GPa	UTS, MPa	UTS, %
SiC/Epoxy	5HS	66 <sub>±</sub> 4	0.06 <sub>±</sub> 0.015	116 <sub>±</sub> 21	328 <sub>±</sub> 30	0.7 <sub>±</sub> 0.07
SiC/MoSi <sub>2</sub> -SiC	PW	37 <sub>±</sub> 4	0.03 <sub>±</sub> 0.004	131 <sub>±</sub> 7	264 <sub>±</sub> 20	0.7 <sub>±</sub> 0.07
SiC/MoSi <sub>2</sub> -SiC	5HS	62 <sub>±</sub> 26	0.05 <sub>±</sub> 0.021	125 <sub>±</sub> 24	329 <sub>±</sub> 52	0.5 <sub>±</sub> 0.09
SiC/MoSi <sub>2</sub> -SiC	8HS	49 <sub>±</sub> 3	0.03 <sub>±</sub> 0.003	160 <sub>±</sub> 3	304 <sub>±</sub> 8	0.8 <sub>±</sub> 0.04
SiC/SiC	5HS	105 <sub>±</sub> 12	0.05 <sub>±</sub> 0.01	215 <sub>±</sub> 18	340 <sub>±</sub> 26	0.8 <sub>±</sub> 0.05

modulus of SiC/MoSi<sub>2</sub>-SiC composites may be due to microcracking of the matrix due to large difference in thermal expansion between MoSi<sub>2</sub> and SiC particles.

The SEM photographs of the fracture surfaces of SiC/MoSi<sub>2</sub>-SiC composites are shown in Fig. 3. The fracture surface is jagged with limited fiber pull out.

### Thermal conductivity

The variation of transverse thermal conductivity with temperature in argon is plotted in Fig. 4 for Hi-Nicalon SiC/MoSi<sub>2</sub>-SiC and SiC/SiC composites. At room temperature, the transverse thermal conductivity for SiC/SiC composites is

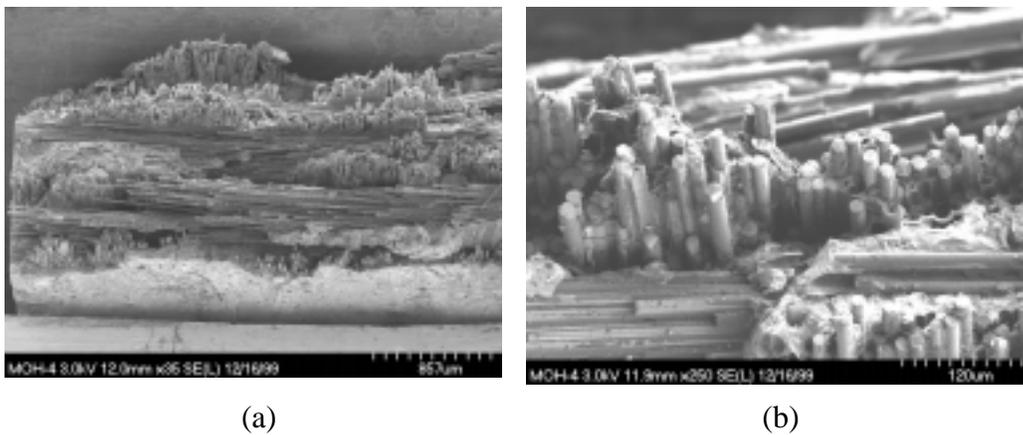


Fig. 3 SEM photographs of the tensile fracture surface of the 5HS Hi-Nicalon SiC/MoSi<sub>2</sub>-SiC composites.

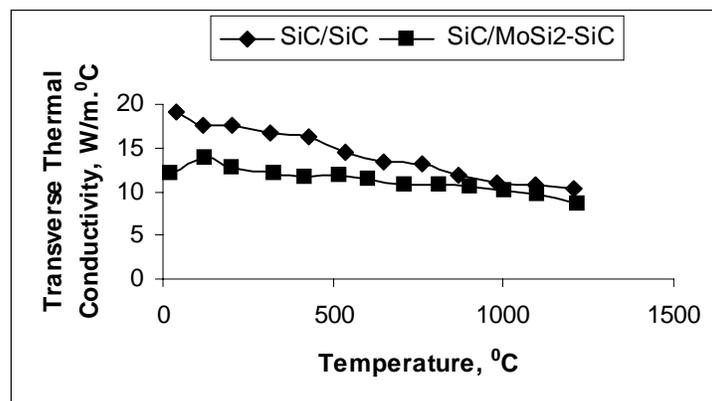


Fig. 4 Variation of transverse thermal conductivity with temperature for the Hi-Nicalon SiC/MoSi<sub>2</sub>-SiC composites and SiC/SiC composites in argon.

higher than that for the SiC/MoSi<sub>2</sub>-SiC composites. As test temperature increases, the difference between the thermal conductivity of these two materials decreases, and beyond 1100<sup>0</sup>C, the thermal conductivity of both materials is nearly the same.

## SUMMARY OF RESULTS

Hi-Nicalon SiC fiber reinforced MoSi<sub>2</sub>-SiC composites have been fabricated by the MI process. The thermal conductivity and room temperature tensile strengths of the SiC/MoSi<sub>2</sub>-SiC composites have been measured and compared with state-of-the-art SiC/SiC composites fabricated by a similar processing method. Major findings are the following.

- (1) Microstructurally, the Hi-Nicalon SiC fiber and the CVI SiC coating are stable during MI processing of the SiC/MoSi<sub>2</sub>-SiC composites.
- (2) Matrix dominated properties such as the primary elastic modulus and DFL stress for the SiC/MoSi<sub>2</sub>-SiC composites are lower than those for the SiC/SiC composites, possibly due to microcracking of the matrix.
- (3) High temperature thermal conductivity of the SiC/MoSi<sub>2</sub>-SiC composites is similar to that of the SiC/SiC composites.

## REFERENCES

- <sup>1</sup> High Temperature Structural Silicides, edited by A. K. Vasudevan, and J. J. Petrovic, (Elsevier Science Publishers, Amsterdam, 1992); *Mat. Sci. Eng.*, **A155**, 1-274 (1992).
- <sup>2</sup> J. J. Petrovic, and R.E. Honnell, *Ceram. Eng. Soc. Proc.*, **11**,734 (1990).
- <sup>3</sup> D. M. Shah, and D. L. Anton, US Air Force Report WRDC-TR-90-4122, Feb. 1991.
- <sup>4</sup> E.Fitzer, and W. Remmele, 5<sup>th</sup> Int. Con. On Composite Materials, ICCM-V, AIME, 515 (1985).
- <sup>5</sup> M.J. Maloney, R.J. Hecht, in High Temperature Structural Silicides, edited by A. K. Vasudevan, and J. J. Petrovic, (Elsevier Science Publishers, Amsterdam, 1992); *Mat. Sci. Eng.*, **A155**, 19 (1992).
- <sup>6</sup> M. G. Hebsur, "Development and Characterization of SiC<sub>f</sub>/MoSi<sub>2</sub>-Si<sub>3</sub>N<sub>4</sub>(p) Hybrid Composites" *Mat. Sci. Eng.*, **A261**, 24 (1999).
- <sup>7</sup> M. G. Hebsur, "Pest Resistant MoSi<sub>2</sub> Materials and Method of Making" US Patent, #5,429, 997, 1995.
- <sup>8</sup> A. Muller, G. Wang, R. A. Rapp, in High Temperature Structural Silicides, edited by A. K. Vasudevan, and J. J. Petrovic, (Elsevier Science Publishers, Amsterdam, 1992); *Mat. Sci. Eng.*, **A155**, 199 (1992).
- <sup>9</sup> C. H. Henager Jr., J. L. Brimhall, and J. P. Hirth, "Synthesis of a MoSi<sub>2</sub>-SiC Composite *in situ* Using a Solid State Displacement Reaction," *Mat. Sci. Eng.*, **A155**, 109 (1992).

# REPORT DOCUMENTATION PAGE

*Form Approved*  
*OMB No. 0704-0188*

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

<b>1. AGENCY USE ONLY</b> ( <i>Leave blank</i> )	<b>2. REPORT DATE</b> May 2000	<b>3. REPORT TYPE AND DATES COVERED</b> Technical Memorandum	
<b>4. TITLE AND SUBTITLE</b>  Processing and Properties of SiC/MoSi <sub>2</sub> -SiC Composites Fabricated by Melt Infiltration		<b>5. FUNDING NUMBERS</b>  WU-523-31-13-00	
<b>6. AUTHOR(S)</b>  Ramakrishna T. Bhatt and Mohan G. Hebsur			
<b>7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)</b>  National Aeronautics and Space Administration John H. Glenn Research Center at Lewis Field Cleveland, Ohio 44135-3191		<b>8. PERFORMING ORGANIZATION REPORT NUMBER</b>  E-12230	
<b>9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)</b>  National Aeronautics and Space Administration Washington, DC 20546-0001		<b>10. SPONSORING/MONITORING AGENCY REPORT NUMBER</b>  NASA TM-2000-210033	
<b>11. SUPPLEMENTARY NOTES</b>  Prepared for the 24th Annual Conference on Composites, Advanced Ceramics Materials, and Structures sponsored by the American Ceramic Society, Cocoa Beach, Florida, January 23-28, 2000. Ramakrishna T. Bhatt, U.S. Army Research Laboratory, NASA Glenn Research Center; Mohan G. Hebsur, Ohio Aerospace Institute, 22800 Cedar Point Road, Brook Park, Ohio 44142. Responsible person, Ramakrishna T. Bhatt, organization code 5130, (216) 433-5513.			
<b>12a. DISTRIBUTION/AVAILABILITY STATEMENT</b>  Unclassified - Unlimited Subject Category: 24  This publication is available from the NASA Center for AeroSpace Information, (301) 621-0390.		<b>12b. DISTRIBUTION CODE</b>  Distribution: Nonstandard	
<b>13. ABSTRACT</b> ( <i>Maximum 200 words</i> )  Hi-Nicalon SiC fiber reinforced MoSi <sub>2</sub> -SiC matrix composites (SiC/MoSi <sub>2</sub> -SiC) have been fabricated by the melt infiltration approach. The composite consists of ~60 vol%, 2-D woven BN/SiC coated Hi-Nicalon SiC fibers and ~40 vol% MoSi <sub>2</sub> -SiC matrix. The room temperature tensile properties and thermal conductivity of the SiC/MoSi <sub>2</sub> -SiC composites were measured and compared with those of the melt infiltrated SiC/SiC composites. The influence of fiber architecture on tensile properties was also evaluated. Results indicate that the primary modulus, stress corresponding to deviation from linearity, and transverse thermal conductivity values for the SiC/MoSi <sub>2</sub> -SiC composites are significantly lower than those for the SiC/SiC composites. Microcracking of the matrix due to the large difference in thermal expansion between MoSi <sub>2</sub> and SiC appears to be the reason for the lower matrix dominated properties of SiC/MoSi <sub>2</sub> -SiC composites.			
<b>14. SUBJECT TERMS</b>  Composites; Properties: Processing; MoSi <sub>2</sub> -SiC system		<b>15. NUMBER OF PAGES</b> 15	
		<b>16. PRICE CODE</b> A03	
<b>17. SECURITY CLASSIFICATION OF REPORT</b> Unclassified	<b>18. SECURITY CLASSIFICATION OF THIS PAGE</b> Unclassified	<b>19. SECURITY CLASSIFICATION OF ABSTRACT</b> Unclassified	<b>20. LIMITATION OF ABSTRACT</b>